

The state of the art in hydrogen storage.

REYNOLDS, J., ALI, D. and NJUGUNA, J.

2023

The state of the art in hydrogen storage

Jemma Reynolds^{1,2*}, Dallia Ali^{1**} and James Njuguna^{1,2***}

¹Advanced Materials Research Group, School of Engineering, Robert Gordon University, Sir Ian Wood Building, Aberdeen, AB10 7GJ, United Kingdom

²National Subsea Centre, 3 International Ave., Dyce, Aberdeen, AB21 0BH

*Corresponding Author Email: j.reynolds5@rgu.ac.uk

** Corresponding Author Email: d.ali@rgu.ac.uk

***Corresponding Author Email: j.njuguna@rgu.ac.uk; Tel. +44 (0) 1224262304

Abstract

The global renewable energy mix is set to change even further with the increasing demand for hydrogen. The production levels are dramatically increasing, and it is becoming prevalent that the storage of hydrogen gas is much more complex than natural gas. There are many different hydrogen storage options being investigated, trialled, and used within the energy industry. On land storage of hydrogen use compressed pressure vessels for gas, cryogenic storage for liquid hydrogen and the blending of hydrogen into natural gas to be stored in current pipeline systems. Underground storage options are found in depleted hydrocarbon reservoirs, deep aquifers, and salt caverns. The storage of hydrogen gas presents numerous challenges and opportunities as discussed within this paper, such as design and manufacturing, hydrogen embrittlement and behaviour, structural integrity, standards and regulation, safety of high-pressure storage, subsea storage and circular economy prospects in structural design. Numerous types of vessel compositions have been explored for the most suitable materials combination in pressure vessel designs, with type IV being the most widely used. However, there are many aspects of the vessel design that have areas for improvement to store hydrogen at a higher efficiency. There are also many opportunities for further developments in hydrogen storage, such as subsea storage and circular economy incorporated designs.

Keywords

Hydrogen storage, composite materials, compressed gaseous hydrogen, structural integrity

Contents

1. Introduction	4
2. Types of storage	5
2.1 Storage vessels for hydrogen (small/large-scale Above ground/ man-made)	5
2.1.1 Compressed gas storage	6
2.1.2 Liquified hydrogen storage	10
2.1.3 Solid Material based storage	12
2.2 Large Scale Storage (Underground)	14
2.2.1 Depleted hydrocarbon reservoirs	17
2.2.2 Deep Aquifer	18
2.2.3 Salt Caverns.....	18
2.2.4 Pipelines	19
3. Challenges, Opportunities and future prospective	20
3.1 Compressed gas pressure vessels manufacturing Process	21
3.2 Materials, design and manufacturing	21
3.3 Structural integrity due to structural impact failure.....	23
3.4 Standards and regulations of structural design	26
3.5 Safety risks due Operational to high pressure	30
3.6 Subsea storage and pipeline blending	30
3.7 Efficiency, cost and circular economy prospects in structural design	31
4. Conclusion	31
References	32

Abbreviations

RE	Renewable Energy
CCS	Carbon Capture and storage
PEM	Proton Exchange Membrane
MMC	Metal matrix composites
CMC	Ceramic matrix composites
PMC	Polymer matrix composites
LVI	Low velocity impact
LDPE	Low Density polyethylene
HDPE	High density polyethylene
LLDPE	Linear low-density polyethylene
RTM	Resin Transfer Moulding
CFR	Carbon fibre reinforced polymers
GFRP	Glass fibre reinforced polymers
COPV	Composite overwrapped pressure vessels
FPSO	Floating production storage and offloading
FRP	Fibre reinforced plastics tanks
FE	Finite element
SEM	Scanning Electron Microscopy
HE	Hydrogen Embrittlement

1. Introduction

The proportion of renewable energy production is on the rise to address energy and environmental issues. However, renewables like wind and solar face local limitations and supply-demand inefficiencies. To overcome these challenges, suitable secondary storage systems are needed, and hydrogen is a promising option. Hydrogen gas is a clean alternative to natural gas and is abundant, making up 75% of the universe's mass. It offers endless potential as an energy source and can be produced through various methods.

Hydrogen, being the simplest form of all molecules, possesses the lowest energy content per unit volume. However, it holds the highest energy content among all fuels when considering weight. This high energy content makes hydrogen a valuable fuel in various applications like fuel cells and rockets. Hydrogen offers significant advantages, such as being emission-free, which addresses issues with fossil fuels, and having a heating value three times higher than petroleum. However, a key challenge in advancing fuel cell vehicles is hydrogen storage. Its low energy density makes it difficult to store enough hydrogen without the storage container becoming too large or heavy. As a result, research on hydrogen storage techniques, including pressurized tank storage, metal-based compound uptake, cryogenic liquid hydrogen storage, and underground storage systems, is crucial for the development of fuel cell vehicles. Consequently, the demand for hydrogen has grown more than threefold since 1975 [1] (Figure 1), and the potential uses of hydrogen range from industrial steel production, decarbonisation of industries, transportation fuel for buses, cars, airplanes and energy storage. Investment plans and governments worldwide have committed more than 70 billion USD in public funding to date [1].

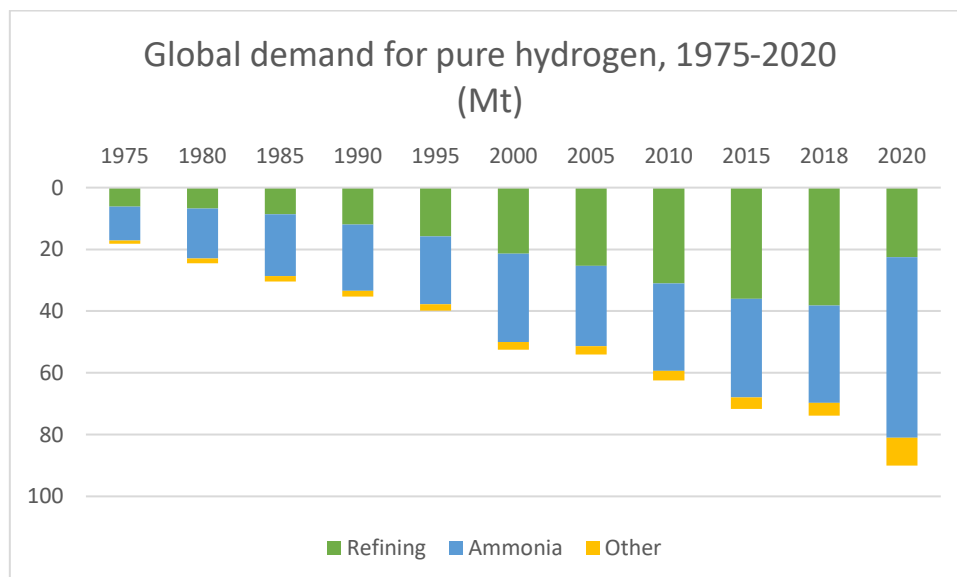


Figure 1: Global demand of pure hydrogen from 1975-2020 (Source: [1])

This is due to the fact that hydrogen as an energy source can help renewables contribute an even greater quota of energy than they are providing currently. This can be achieved using hydrogen to store renewable energy during a period of low demand phases. In all, hydrogen storage development will combat the issues regarding the intermittency associated with renewable energy production, help balance grid supply and support the transport

infrastructure. Hydrogen storage is prevalent in all aspects of the process, from production to storage, to transportation to utilisation.

Significant research is focused on utilizing mobile storage vessels and vehicle fuel cells for hydrogen. However, there are challenges in transforming the infrastructure for large-scale hydrogen use. Various hydrogen distribution pathways exist, including cryogenic liquid trucks, compressed tube trailers, and gaseous pipelines [2]. Tube trailers could be crucial during the initial phase of introducing liquid hydrogen into the energy mix, as they can accommodate smaller demand and avoid boil-off issues associated with liquid hydrogen storage.

Advanced materials for high-pressure gas storage vessels are witnessing rapid growth, making it one of the largest and most rapidly expanding markets. The purpose of this paper therefore is to review the current hydrogen storage options, including compressed gas storage, and highlight the opportunities and future prospects for hydrogen storage using advanced materials to support ever growing demand.

2. Types of storage

Hydrogen storage systems which support renewable energy production can overcome intermittency problems and high cost transmission, providing a stable source of base load energy.

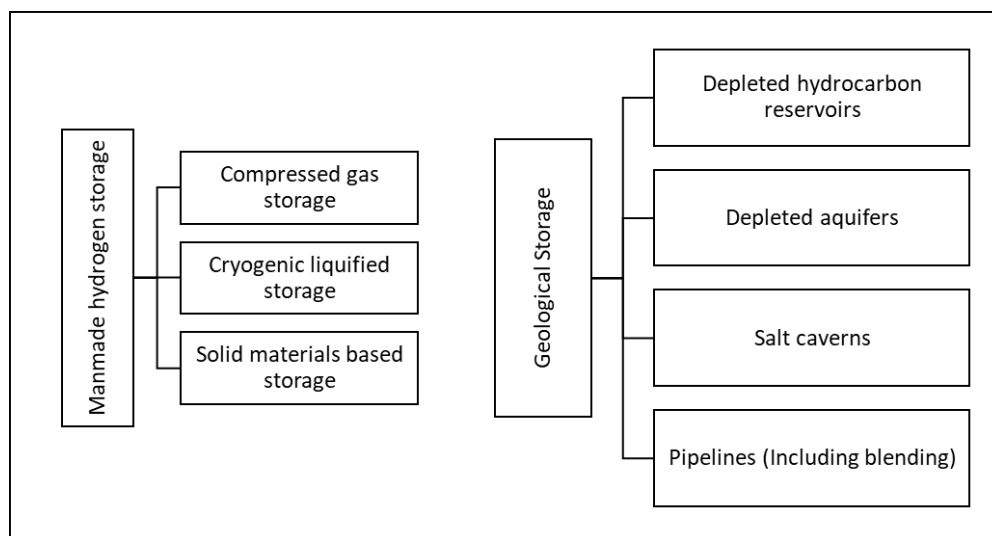


Figure 2: Overview of the types of man-made and geological hydrogen storage covered in this paper, (Source: adapted [3])

2.1 Storage vessels for hydrogen (small/large-scale Above ground/ man-made)

Hydrogen in gaseous form offers the advantage of compact storage with retained energy effectiveness, and the technology is relatively simple. Increasing the pressure enhances the energy density per volume, allowing for efficient storage in a small space. However, this process can be volumetrically and gravimetrically inefficient as discussed in detail in the following sections [4].

2.1.1 Compressed gas storage

High-pressure gas cylinders are widely used for hydrogen storage, primarily because of their technical simplicity, rapid filling and release rates, cost-effectiveness, and well-established maturity of the method [5]. The high-pressure gas cylinder system has a life expectancy of around 20 years. Despite this storage method being the cheapest method (around 10,000 \$ in capital), there are many drawbacks. Due to hydrogen being the lightest element in the world, issues arise with volumetric density, the tank pressures and overall efficiency. Unfortunately increasing the pressure within the gas tank only provides slight benefits. In some cases, the increased pressure by increasing the thickness of the walls of the pressure cylinder decreases the gravimetric density of the hydrogen [6]. The pressure vessels necessitate a three-layer structure, comprising an inner polymer liner, a carbon fiber composite overwrap, and an outer aramid layer that offers resistance to mechanical and corrosion-related damages [7]. Compressing hydrogen can be achieved using conventional mechanical compressors of the piston type, with minor adjustments made to the seals to accommodate the higher diffusivity of hydrogen. The most optimized trade-off between cost-effectiveness and storage pressure for hydrogen cylinders is achieved at around 50-55MPa. However, lighter weight composite cylinders can withstand pressures up to 80MPa, enabling hydrogen to achieve a volumetric density of 36 kg/m³ [8].

In terms of storage vessel design and manufacture, this is dependent on the production capacity of the system, and the technological development of the production process identified. As with the production vessels, storage of hydrogen also depends on the capacity and system used. In simple terms the higher the gas pressure, the lower the storage volume needed. Currently, there are different types of pressurized fuel tanks developed for the compressed gas, normally classified as Type I, II, III and IV [9] [10] [11] [12]. However, design limitations are experienced when using steel due to hydrogen embrittlement (cracking caused by hydrogen migrating into the metal) [13].

Type I are known as monolithic pressure vessels and are full metal pressure tanks. They are made of standard aluminium or high strengthened steel, withstanding a maximum pressure of 17.5-20 MPa. These tanks are susceptible to fatigue, damage, and corrosion; therefore, their life is predictable. They possess very high compressional design strength and exhibit properties that provide high impact strength. The main drawback of this type is the heavy weight meaning they are used for stationary purposes. Type I tanks are typically used for scuba diving and within the manufacturing industry.

Type II was the first model to be designed as a composite pressure vessel to be a lightweight alternative to type I. Type II consist of glass-, aramid-, or carbon fibre-reinforced composite (FRC) which is hoop wrapped on the vessel. This composite wrapping helps to retain the hoop stress. The retained stress is shared with the metal liner which allows the metal wall to have a reduced thickness. The composite material does not possess the complete stress loads of the cylinder, therefore the metal liner is needed to withstand the pressure by retaining the required strength. These pressure tanks can withstand around 26.3-29.9 MPa. The advantage of using composite materials is the reduced weight of the cylinder, however there are additional costs for manufacturing composites and certification. Fibre-reinforced composite

(FRC) tanks have been widely used for water storage and in offshore mostly for storing fluids such as diesel and lube oil. The literature shows that FRC tanks perform better than aluminium or steel tanks due to their low thermal conductivity, the contents of the composite tank remain cooler, and they have also shown to be leak free characteristics for a longer time in hydrocarbon pool fire [14]. Type II tanks are often used for water storage and offshore for diesel and oil. The outer composite layer protects the tank from environmental damage however hydrogen embrittlement would still occur within the metal inner layer.

Type III vessel design consists of a metal liner (mostly aluminium alloy to prevent oxidation corrosion) and is overwrapped by a composite layer. This fibre-reinforced composite overlay consists of hoop and transverse wrap on the cylinder and mostly use glass, aramid or carbon fibre. These pressure tanks can withstand an approximate pressure of 30.5 MPa and 70 MPa for aluminium alloy / glass-fibre reinforced composites (GFRC) and for aluminium alloy / carbon-fibre reinforced composites (CFRC) respectively. The advantage of this cylinder is its reduced weight with reduction in the thickness of the metal liner. The metal liner acts as a membrane to contain the pressurised gases. The composite overlay can only retain the stress of the compress gas as the composite possess a very high modulus of elasticity compared to the metal liner. This allows the composites overlay in taking the heavy load in the structure. Type III tanks have a higher percentage of composite material which allows the cylinder to be even lighter than Types II and store minimal amounts of hydrogen. Aluminium alloy layers play a fundamental role in design and performance of composite high-pressure hydrogen storage vessels. Type III tanks are often used as medical oxygen cylinder in ambulances or in homes, within the aerospace and military sectors.

Type IV vessel consists of a plastic-lined pressure vessel which is overwrapped with a composite material and the structural strength and stiffness are provided by the composite. The function of the plastic liner is to contain the gas. The liner is made from high density polythene to prevent corrosion, better fatigue resistance and hydrogen embrittlement rate than metals. The modulus of elasticity for the plastic liner and the composite overwrap is spread in such a way that it ensures minimum fatigue on the plastic membrane. However, these plastic liners fail to provide a rigid supporting membrane to the composites. Therefore, this type of cylinders is more susceptible to impact damage. They are the lightest compared to the other vessels. Type III and type IV tanks are considered as the most appropriate solutions for transportation storage containers [15]. Gases, such as natural gas and air are transported using these types of storage tanks, accounting that high pressure is required for transporting hydrogen (35 to 70 MPa), whereas natural gas and air only require up to 30 MPa. Conversely, these storage containers do not satisfy requirements in the automobile industry due to high cost and low performance. Type IV vessels are often used for gas transportation and storage.

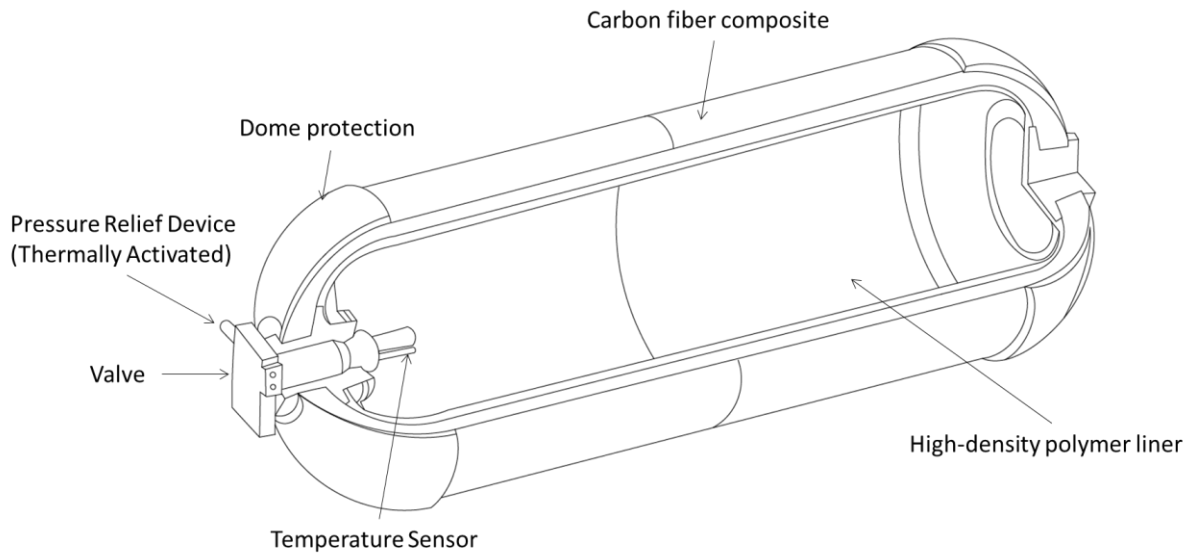


Figure 3: Type IV Composite overwrapped hydrogen pressure vessel (Source: [16])

Developments of Type V composite tanks were recently introduced and have undergone successful testing [17]. The type V design offers an all-composite construction with a liner-less design, with composite fiber wound over a sacrificial mandrel [18]. Compared to a type IV composite vessel the type V is 10-20% lighter and similarly 100% load bearing. However very little research has been focused on type V vessels, hence further developments required commercialisation of those pressure vessels.

In terms of oil and gas sector, composite materials and tanks are nowadays used on offshore structures and Floating Production Storage and Offloading's vessel due its light-weight structural properties high pressure uses which composite compressed cylinders ranging from 35-150MPa as shown on Table 1 [19].

Table 1: Current applications of composites for offshore

Current applications of composites offshore	
Composite Grids/ Gratings	Cable support systems
Handrails and Ladder Components	Modular panelling for partition walls
Aqueous Piping System	High pressure accumulator bottles
Water and fuel storage tanks, Vessels	Flexible and Floating Risers, Drill pipe
Low pressure composite valves	Sub – sea structural components
Spoolable type thermosetting tubes	Boxes, housings and shelters
Sump Caissons and pull tubes	Tendons
Blast Protection	Fire Protection
Fire water pump casing and sea water lift pump casing	Offshore bride connecting between platforms

There is a need to continue exploring low cost affordable manufacturing techniques coupled with ability for mass production and a reduction in part number count and significantly improved structural integrity. Improvement of gas permeability may be achieved by using novel materials and nanocomposites in a composite tank.

Table 2: Comparison of pressurised fuel tanks with applications [9] [10] [11] [12]

	Type I	Type II	Type III	Type IV
Overview	Full metal pressure tanks Standard aluminium or high strengthened steel.	Composite fibre which is hoop wrapped on the vessel.	Metal liner (mostly aluminium to prevent oxidation corrosion) and is overwrapped by a composite layer	Plastic-lined pressure vessel which is overwrapped with a composite material.
Pressures	Withstanding a maximum pressure of 175-200 bars	Can withstand around 263-299 bars	Can withstand an approximate pressure of 305 bars for aluminium/ glass, and 700 bars for aluminium / carbon fibres.	Can withstand 350 to 700 bar
Advantages	Very high compressional design strength and exhibit properties that provide high impact strength	Provide optimum safety and are light weight. Saves up to 75% of the weight compared to metal cylinders. Very good behaviour in fire, impact accidents and are corrosion free from inside and outside. Capable of large diameters whilst less costly than seamless metal liners. Low thermal conductivity, the contents of the composite tank remain cooler.	Type III tanks have a higher percentage of composite material which allows the cylinder to be even lighter than Types II. Reduced weight with reduction in the thickness of the metal liner, composite overlay takes the heavy load	They are the lightest compared to the other vessels.
Disadvantages	Susceptible to fatigue, damage, and corrosion. Heavy weight.	Additional costs for manufacturing and certification		High cost and low performance more susceptible to impact damage as they are less robust, also prone to leakage due to the polymer lining not providing an impermeable barrier.

Applications	Scuba diving Onsite industrial and manufacturing uses	Water storage Used in offshore mostly for storing diesel, lube oil etc	Medical Oxygen cylinders in ambulances and home oxygen therapy Aerospace and military	Transportation storage
--------------	--	---	--	------------------------

2.1.2 Liquified hydrogen storage

When it comes to mobility-based hydrogen, storing and distributing hydrogen in liquid form is considered one of the most practical options from energy, technical, and economic standpoints. This method of storing hydrogen has been recognised as an ideal method the transport sector and has become widely used in space technology for numerous years now [20]. Cryogenic tanker trucks offer the capability to transport larger quantities compared to tube trailers, meeting the requirements of expanding markets. In parallel, pipelines can be strategically positioned to transport hydrogen to high-demand regions as additional production capacities are established.

Liquefaction involves cooling a gas to convert it into a liquid, utilizing a combination of compressors, heat exchangers, expansion engines, and throttle valves. The Linde cycle or the Joule-Thomson expansion cycle are the most straightforward methods for liquefaction processes. Liquid hydrogen has benefits such as its low molecular weight and high energy output, for this reason it has become a mature technology as a propulsion fuel in aircraft and aeronautical vehicles [2]. Liquid hydrogen tanks are recommended for their ability to store 0.070 kg/li of liquid hydrogen, whereas its compressed gaseous form can only store 0.030 kg/li. [21]. Hydrogen storage is gravimetrically and volumetrically efficient, but further research is required to address challenges related to hydrogen uptake and release, high liquefaction rates leading to significant energy loss, hydrogen boil-off, and expensive tank costs.

It is recognised that liquid hydrogen is stored in cryogenic tanks at -251.95 which is roughly around -253°C and at ambient pressure [22]. Cryogenic vessels have been a common choice for storing and transporting industrial gases for over four decades. To liquefy hydrogen, the gas must be refrigerated at extremely low temperatures, necessitating highly efficient and well-insulated vessels. Modern developments in the manufacturing and design of cryogenic tanks have significantly reduced the thickness of the vessel walls, whilst the limiting of expensive material usages (such as stainless steel) has reduced the overall vessel price. These design and manufacturing methods (cold stretching) have now been standardised through the ISO 21900-1 [23]. To manage storage at -253 °C, high efficiency insulated vessels and an external protective jacket are implemented into the vessel designs. In addition, perlite or super insulation is employed to decrease the thermal conductivity within the space between the inner vessel and the outer jacket. This insulation can take the form of a powder structure or involve wrapping with layers of aluminium films [24]. Liquid hydrogen transportation via roads is carried out using trucks which can exceed a capacity of 60,000 L. The method of

transportation depends on the required quantities, which can be achieved through vacuum insulated containers or transferring the product to stationary vessels. For intercontinental transport, large ships are utilized to carry the liquid form of hydrogen, allowing for the accommodation of the size of the tanks used.

Energy efficiency concerns arise in both the liquefaction process and the thermal insulation of cryogenic vessels to minimize hydrogen boil-off. As mentioned previously, the rate of hydrogen boil-off from a liquid storage vessel, caused by heat leaks, is influenced by factors such as size, shape, and thermal insulation [25]. Since boil-off losses due to heat leaks are proportional to the surface-to-volume ratio, Boil-off losses in hydrogen storage decrease as tank size increases due to the surface-to-volume ratio. Spheres are the ideal shape for liquefied hydrogen storage, distributing stress and strain evenly, but large-sized spherical containers are expensive to manufacture due to complexity. Advanced insulating techniques are necessary to maintain low temperatures, making this method impractical and costly for small-scale applications [26].

In comparison with hydrogen gas, up to 40% of the energy content in hydrogen liquid can be lost whereas in gas there is only a 10% energy loss [27]. The reduction in temperature of hydrogen gas can be very time consuming and highly energy intensive. The advantage of liquid hydrogen is that it has three times the energy to mass ratio than in its gaseous form, making it the most energy dense fuel. Hydrogen in its liquid form can be very difficult to store over long periods due to the product loss by vaporisation and requires large bulky tanks due to the insulation needs [28][4]. Table 1 provides an overview on storage advantages and disadvantages in both liquid and gases form. In its gaseous form, compressed hydrogen can be stored in high pressure tanks.

Table 3: Hydrogen Liquid vs Gas (Advantages and Disadvantages) [21]

	Advantages	Disadvantages
Liquid References:	Can store more than gas per m ³	Requires conversion at either side of the storage process
	Easier to transport	The cooling process for liquefaction demands a substantial amount of energy, with energy consumption during liquefaction accounting for approximately 30% of the total hydrogen energy in practical applications.
	Higher energy output	Chance of evaporation if not kept below its critical temp
	Low density as a liquid	Achieving thermal insulation for the vessel presents challenges, and the chosen design must meet strict criteria to effectively control evaporation losses of liquid hydrogen in the inner vessel and ensure the safety of the storage container, considering factors like anti-

		freezing capabilities and pressure-bearing capabilities.
	Mature technology as a propulsion fuel in aircraft and rockets	High liquefaction rate that causes energy loss (25%-40%)
		High cost (\$14.25/kg)
Gas References:	Does not need converting either side of the storage process	Very expensive materials to maintain tanks with 70MPa
	Simple and mature technology	Volumetrically and gravimetrically inefficient
	Stored in smaller space	
	Low storage energy consumption	
	Low cost at not too high pressure	
	High speed of hydrogen release and inflation, at room temperature	

2.1.3 Solid Material based storage

Materials-based hydrogen storage methods can significantly increase the density of hydrogen, surpassing the storage capacity of liquid hydrogen by more than two times. Metal hydride-based energy storage offers a compact and efficient way to store hydrogen at ambient temperature and moderate pressure, providing an energy density approximately three times higher than compressed or cryogenic storage. This is achieved through an extremely high volumetric density within the host lattice [29] [30]. Metal hydride storage systems are significantly more compact, being up to 18 times smaller than gaseous hydrogen storage systems, while holding the same amount of hydrogen. They possess the ability to absorb considerable amounts of hydrogen at a constant pressure, thanks to phase transition properties.

The common design for metal hydrogen storage tanks is made up of stainless steel or aluminium and copper aspects shown in figure 5. The tube of the tanks is stainless steel, along with end caps and filters. However, the spiral heat exchanger is made from copper. Paster et al showed that the tanks are not completely filled with hydride powder as some space is required for expansion volume as the metal lattices expand during the absorption process [31]. It is suggested that 85% of the inner volume is a reactional volume, with 12% of free volume for the expansion, with 3% occupied by the internal heat exchanger [32].

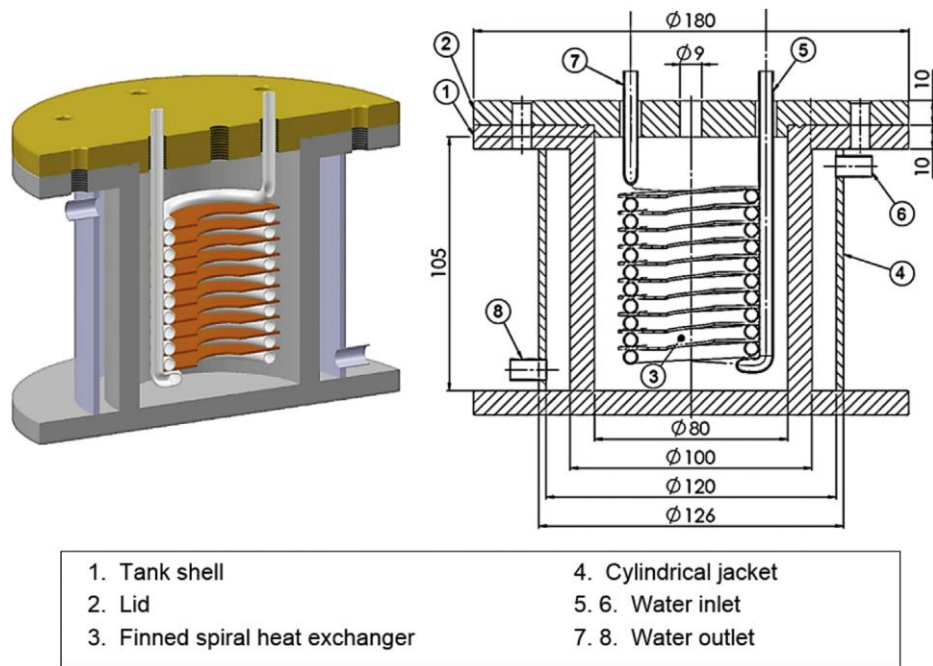


Figure 4: Schematic of the hydride tank used for hydrogen storage (Source: [31])

Souahlia et al [33] demonstrate that A metal hydride storage tank consists of a hydrogen storage alloy powder, heat exchange parts, and gas transport components. The container body is typically made of aluminium alloy or stainless steel. Metal hydrides, formed through a reversible reaction between gaseous H₂ and certain metals or alloys, hold great potential for hydrogen storage as solid-state materials. They offer exceptionally high volumetric hydrogen storage density, exceeding 100gH/L in a given volume of solid-state material. These tanks, employing welded stainless-steel structures, can withstand hydrogen pressures of up to 185 bar at temperatures of 150 degrees and up to 500 degrees of short-term heating when not pressurized [34].

Metal hydrides consist of metal atoms forming a host lattice where hydrogen atoms get trapped in interstitial sites. Two fundamental bonding mechanisms have been identified for material-based solid-state hydrogen storage[35]. here are two mechanisms for material-based solid-state hydrogen storage. The first is chemisorption (absorption), where H₂ molecules are dissociated into H₂ atoms and integrated into the material's lattice, allowing for large storage in small volumes under low pressure and ambient temperatures (Figure 11). The second mechanism is physisorption (adsorption), where hydrogen atoms or molecules attach to the material's surface. Preferred material characteristics include high gravimetric and volumetric capacity, reversible hydriding, favourable equilibrium temperature and pressure properties, low sensitivity to gas impurities, and adequate stability within the formed hydride [36]. Hydrogen can be combined with various metals to form hydrides that release hydrogen upon heating [37]. Materials for hydrogen storage fall into two categories: hydrides (hydriding alloys, molecular hydride complexes, amine complexes, and hydrocarbons) and physisorbed high-surface-area materials (carbon fullerenes, nanotubes, metal organic frameworks, and aerogels). The uptake capacity of hydrogen in hydrides depends on temperature, pressure, and alloy composition [38]. Low temperature hydrides

can be found in iron titanium (FeTi) and magnesium-based hydrides (Mg₂Ni) work at a higher temperature [39]. The lifecycle of the hydrides is considerably affected by the impurities present in the hydrogen being stored. Research shows [40] that after 500 cycles a drop of almost 50% of the capacity is noticed, however cycling pure hydrogen with a magnesium hydride enables restoration. Material-based hydrogen storage methods operate at low pressures, and hydrides require additional energy for hydrogen release. The advantage lies in the reversibility of formation and decomposition reactions, allowing hydrides to be decomposed at moderate temperatures, potentially sourced from local and renewable heat sources like solar energy. Economically, this storage approach is cost-effective, with moderate storage vessel costs, low operating and maintenance expenses, and low purchased energy requirements per storage cycle [40].

Both absorption and adsorption methods have their pros and cons. Absorption requires thermal management to supply or remove heat for the reaction of splitting or recombining hydrogen molecules and forming chemical bonds with the material. The ability to recycle or reuse the heat is crucial for system efficiency [35]. On the other hand, adsorption faces challenges in finding a light carrier with enough bonding sites and the need for low temperatures [41]. Despite these challenges, the advantages of the adsorption method include low operating pressures, inexpensive materials, and a straightforward storage system design. The success of hydrogen as a future fuel heavily relies on the optimal thermal design of materials suitable for reversibility [42].

2.2 Large Scale Storage (Underground)

The use of geological formations deep underground covered by several hundred meters of rock allow for the use of high pressures up to 20MPa. These facilities allow for large storage volumes and capacities, with low investment costs [43]. The principle behind hydrogen storage in geological storage is the injection of hydrogen gas underground and its storage under pressure [44]. This will enable the hydrogen gas to be stored and removed when there is a need for it. Storage of hydrogen gas underground is advantageous because while it is stored underground it is safe and secure since they are preserved to be less vulnerable to fire issues, military and terrorists' threats [45].

The underground storage of hydrogen if done properly can also aid in smooth urban planning because it does not affect planning of urban planning [3]. Underground storage of hydrogen is also more economical compared to other pressured composite and steel vessels for hydrogen storage, underground storage of hydrogen has great potential to reduce hydrogen storage costs.

It follows that the general trend seen in research is that a higher volumetric storage density is correlated with a high gravimetric storage density. However, surface hydrogen storage facilities in the form of tanks and pipelines have limited storage and discharge capacities therefore the large-scale storage solutions are realised underground [46]. The benefits of storing hydrogen on a large scale have been realised in engineering practices already, meaning in the future when the use, storage and distribution of hydrogen is common practice

there will be well developed set of codes and standards in place [46]. This highlights the many reasons for storing very large quantities of gas underground in geological formations.

The expenses of a large-scale hydrogen storage system can be categorized into three components: construction costs of the storage facility, operational costs of utilities, and maintenance costs [25]. Investment costs are influenced by storage density, with volumetric hydrogen storage density determining storage size and gravimetric hydrogen storage density determining the amount of storage material needed per unit weight of hydrogen stored.

There are limited similarities of hydrogen gas to natural gas, meaning adaptations are required due to the characteristics of hydrogen in high concentrations and under high pressures, especially when it comes to the use of metal pipelines, as hydrogen can cause hydro-blistering, cracking and hydrogen embrittlement [47]. This biggest difference can be seen within the permeability index differences between hydrogen and natural gas, suggesting that hydrogen has a permeability index 5 times higher than that of methane and natural gas [48]. Due to the nature of hydrogen gas, underground storage has been the favoured option and there are several options within this concept. There are many advantages to underground storage of hydrogen gas, it is a safe alternative to on-land storage due to being less susceptible to fires and general attacks. Traditional surface tanks require extensive areas to store the same amount of gas as underground storage facilities [48]. The latter have minor surface installations, making integration within the current landscape and infrastructure easier. Economically, underground storage offers cost advantages, as construction expenses are significantly lower for facilities of similar capacities compared to surface installations.

Table 4: Large scale hydrogen storage overview, geological and man made [47] [49]

Type	Depleted Hydrocarbon reservoirs
Storage Media	Reservoir rocks characterized by substantial porosity and permeability, accompanied by intact roof rocks serving as effective seals without any fractures
Pressure / temperature	The maximum pressure at the site frequently surpasses the initial reservoir pressure, enabling the storage of larger quantities of gas than initially contained in the deposit.
Access	The presence of deposits in natural geological formations with favourable geological and mining conditions provides opportunities for gas storage. Existing infrastructure on the deposit can be modified and utilized for gas storage purposes. Typically, one to two cycles of gas injection and withdrawal occur each year. A limited number of boreholes are needed for gas injection and withdrawal, along with additional observational boreholes for monitoring purposes.
Reuse	Since the early 1990s, depleted oil wells have been utilized for natural gas storage. The social implications associated with the use of existing or purpose-built underground storage structures hold significant importance for the local communities involved.
Advantages	Depleted natural gas deposits offer the lowest storage costs compared to storing gas in oil fields. In addition, underground storage provides enhanced safety measures with reduced susceptibility to fires, leading to

	lower costs compared to above-surface storage options. Moreover, suitable geological structures for gas storage are widely available across many countries, covering large areas.
Limitations	Converting existing boreholes for hydrogen storage may pose feasibility challenges. The availability of appropriate technology and equipment is crucial for constructing and operating the storage system. The reactivity of hydrogen with liquid hydrocarbons restricts the practicality of utilizing depleted oil fields for storage purposes.
Type	Deep Aquifer
Storage Media	Reservoir rocks characterized by substantial porosity and permeability, accompanied by intact roof rocks serving as effective seals without any fractures
Pressure / temperature	Pressure fluctuations occur during the gas injection and withdrawal processes
Access	The presence of deep aquifers with well-established favourable geological conditions, typically located in proximity to end users, offers opportunities for gas storage. These aquifers do not have existing infrastructure on the deposits. Typically, one to two cycles of gas injection and withdrawal occur each year. A limited number of boreholes are required for gas injection and withdrawal, along with additional observational boreholes for monitoring purposes.
Advantages	Thus far, there have been no documented instances of exclusively storing pure hydrogen in aquifers; most recorded cases involve a mixture of hydrogen and methane gases, typically in a 50/50 ratio.
Limitations	The feasibility of repurposing existing boreholes for hydrogen storage may present challenges. The availability of appropriate technology and equipment is essential for constructing and operating the storage system. However, it is worth noting that the costs associated with adapting boreholes for hydrogen storage tend to be higher compared to storage in salt caverns or hydrocarbon deposits
Type	Salt Caverns
Storage Media	Thick salt formations are considered highly suitable for salt cavern storage.
Pressure / temperature	Rock salt exhibits exceptional gas tightness even under high pressures, making it suitable for operations at depths of nearly 2000m. Operational pressures in this range typically range from 60 to 180 bar. When caverns are located at shallower depths, a smaller volume of cushion gas is required to be permanently present in the cavern. However, reducing the pressure in the cavern leads to compression, limiting the amount of gas that can be injected into it.
Access	The presence of salt deposits with well-established favourable geological and mining conditions provides opportunities for gas storage. These deposits do not have existing infrastructure. There is a potential for multiple cycles of gas injection and withdrawal, ranging up to 10 cycles per year. Typically, one borehole is required for each cavern used for storage.
Limitations	The convergence leading to the compression of the cavern.

	The presence of adequate technology and equipment for constructing and operating the storage system. The accessibility of water for leaching the cavern. Higher expenses compared to utilizing depleted hydrocarbon fields.
Type	Pipes and pipelines
Storage Media	Combination, often metal alloys (steel)
Pressure / temperature	Operate typically at 10-20 bar but can reach up to 2 MPa, dependant on size, diameter and length.
Access	Decommissioned pipelines will have more difficulty being accessed than new pipelines being put in.
Reuse	Decommissioned pipelines are becoming more and more common; however adaptations are required to transform the metal pipelines into a suitable porous media for the control of hydrogen flow, difficult to access as pipelines are buried and costs to remove are high
Advantages	Pipelines act as storage and transportation methods for gas. The storage of energy through a gas network experiences much less loss (<0.1%) than in a power network (8%). When blended with natural gas the natural gas leakage rate reduces slightly due to the higher mobility of hydrogen molecules.
Limitations	Material choices and durability, metal pipes can degrade when exposed to hydrogen over long periods, especially when the hydrogen is in high concentrations (20%+) and high pressures. Hydrogen leakage is a limitation due to the permeation rate for hydrogen, as it is 4 to 5 times higher than that of methane. Leakage occurs mainly through threads or mechanical joints at a rate of 3 times higher than methane

2.2.1 Depleted hydrocarbon reservoirs

Many depleted hydrocarbon fields and reservoirs have been converted into hydrogen storage facilities due to the success of the storage of natural gas. These structures have been around for long geological time periods, validating to tightness of the reservoirs, and the already completed exploration and production phase allows for the parameters to be outlined already. These reservoirs can be at various depths, optimally up to 2000m [48] The reservoir rocks have high porosity and high permeability with inclusion of roof rocks to provide a seal for the deposits. The geology of the reservoir formations is well recognised to have a high capacity for storage, in terms of hydrogen, these fields can hold a similar amount compared to the hydrocarbon that was previously stored. There is a high availability of deposits and the existing infrastructure can be adapted for specific hydrogen gas storage. Depleted hydrocarbon reservoirs can be found in large capacities however their suitability for hydrogen storage is questioned. Despite the existence of remaining natural gas being utilised as cushion gas, the ability for it to mix with pure hydrogen dilutes the hydrogen concentration on output [47].

Literature states that this storage method allows for a maximum of two cycles of injection and withdrawal a year, making it suitable for seasonal storage [49]. Due to the fine matrix of pores in depleted hydrocarbon reservoirs the regular movement of the gas within causes large flow resistances, therefore minimal cycles at low production rates are more suitable. Other limitations that have been identified are within the reactions that take place within the deposits [46]. There can be some contamination of the hydrogen gas with accumulated trapped hydrocarbon residue, and undesired reactions production gases such as hydrogen sulphide (H_2S) and methane (CH_4) causing a loss of hydrogen. From an economic perspective this is the lowest cost option in terms of underground hydrogen storage as there is no need for exploration and construction, however there are more costs in the conversion of depleted oil fields than natural gas storage.

2.2.2 Deep Aquifer

Deep aquifer storage facilities are very similar to hydrocarbon reservoirs; however, they are a layer of water-bearing permeable rock. When converting aquifer storage facilities to suit hydrogen gas several conditions need to be met (Table 4). For example, the top of the aquifer requires sealing by an impermeable layer of rock, a domed shape structure is required to hold the injection of gas in a defined space and there needs to be adequate pore space with high permeability. Each aquifer is judged on an individual basis to assess the suitability of hydrogen storage. However, the advantage of aquifer storage is that there is no chance of contamination of hydrogen with hydrocarbon residues. These storage installations also vary in depth, however optimally up to 2000m with high storage capacity [48]. The geological tightness of the structures is initially unknown which causes a risk of gas leakage and only have the current ability for a maximum of two cycles of injection and withdrawal per year [50]. Economically this storage option is the highest costing in terms of construction and operation due to the amount of exploration and assessment that is required on an individual basis to create suitable storage for hydrogen in its pure form, however on withdrawal it is highly unlikely that hydrogen will be in its pure form due to residual gas, contaminants and mixing. Deep aquifer storages facilities have also been recognised in the potential for carbon capture and storage (CCS) within Europe, however there are no existing examples of this being executed [51].

2.2.3 Salt Caverns

Within Europe there are well recognised salt cavern formations for the storage of natural gas and future hydrogen storage. In the UK there is a fully functioning salt cavern for hydrogen storage in Teeside at 350-450m deep, whilst in the US, Clemens Dome, Spindletop and Moss Bluff are all built at a depth of above 800m. The Teeside salt caverns are storing 1 million m^3 of pure hydrogen, in this instance hydrogen is 96% purity and 4% CO_2 . These salt caverns are at depths of 400m with a pressure of around 5MPa. Literature [47] [46] proves that the characteristics of salt caverns as hydrogen storage can vary significantly across individual installations. Salt caverns can be at various depths, optimally up to 1500m, this depth and the properties associated with salt rock provides a stable tightness of geological formation [48]. Similarly, to other underground storage installations, each storage facility requires one bore hole for the injection and withdrawal of gas, however in the case of salt caverns there is a possibility of multiple cycles of injection and withdrawal of gas per year therefore this method

of storage can be used for more than seasonal storage [52]. There are many limitations to this storage method, there is a possibility of impurities within the gas caused by undesired reactions between the hydrogen and interbeddings other than rock salt [53]. Literature [54] [55] proves that despite it being undesirable it is inevitable that impurities occur in underground hydrogen storage. Within the HyUnder Study [56] five European countries were investigated (Figure 6) suggesting that the number of salt caverns required for 2050 targets are as follows, Germany =74, The Netherlands =43, Spain =24, The UK=21 and Romania= >1. The storage capacity of individual caverns, located in eligible areas within Europe, is estimated based on thermodynamic considerations and site-specific parameters [57].

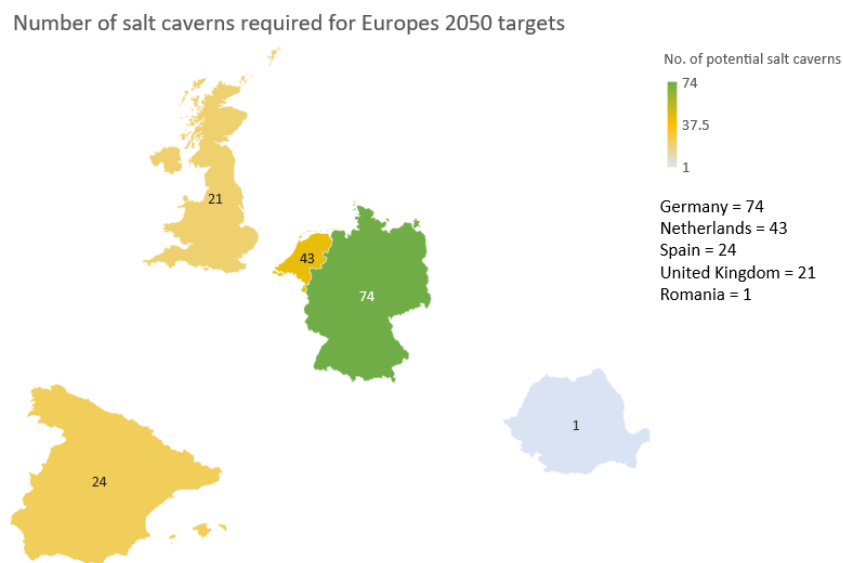


Figure 5: Map showing number of salt caverns required to meeting European 2050 targets (source: [57])

2.2.4 Pipelines

Understanding the implications of hydrogen on pipeline joints and downstream components within the gas grid is crucial to meet the requirements of gas grid operations through the pipeline distribution network. This includes evaluating valves, regulators, and springs to assess the long-term effects of hydrogen on their functional properties. It may be necessary to replace components with new materials or apply hydrogen-resistant coatings. Standardization of testing and inspection protocols for materials research is essential to evaluate the influence of hydrogen blending on pipeline materials and enable transmission through existing pipelines. Hydrogen embrittlement has a more significant impact on high-pressure transmission networks compared to low-pressure distribution networks.

The use of decommissioned oil and gas assets such as pipeline bundles will create a significant increase in overall storage capacity. Pipeline bundles are an economically attractive solution for high pressure, high temperature field development, by incorporating advanced design and

fabrication techniques. However, issues with pipeline storage can be found in the materials used. Hydrogen does not react well with metal pipelines, causing hydrogen embrittlement, hydrogen induced cracking and blistering, therefore alternative materials need to be utilised. Over 75 pipeline bundles are installed in the North Sea and Norwegian sea regions, with the majority installed from Wick, Scotland, with the potential to be included in the UK National Grid HyNTS Programme (Hydrogen in the National Transmission System) [58] .

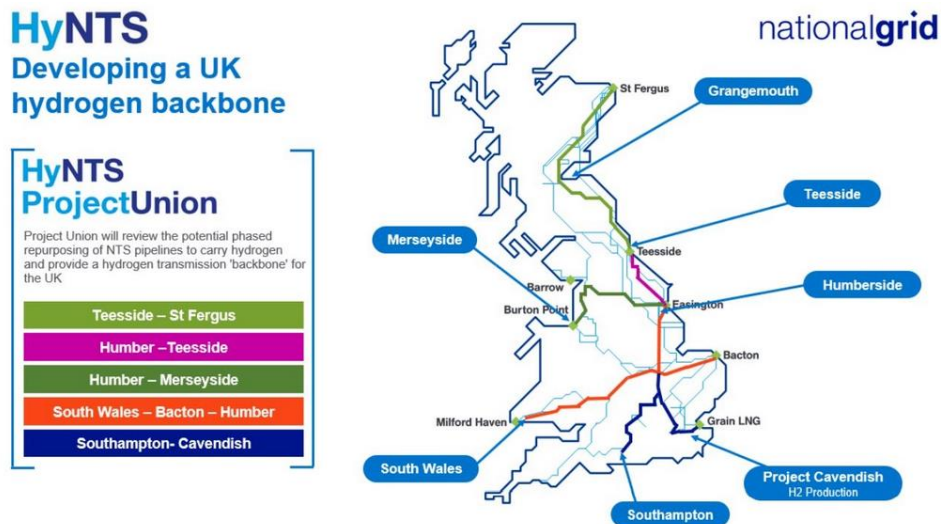


Figure 6: UK National Grid HyNTS hydrogen backbone development (Source: [59])

The natural gas network serves as a permanent storage of hydrogen through blending it into natural gas. Pipeline energy storage offers several advantages, with minimal energy loss (<0.1% compared to 8%) in the gas network. However, using buried pipes for hydrogen storage presents challenges like material durability, hydrogen leaking, and safety concerns (Civan 2004). Hydrogen, being odourless and colourless, lacks detectable smell like natural gas, which has an odorant added for safety. Although non-toxic, hydrogen is highly flammable, posing a serious fire risk in surface storage systems. The material durability of metal pipes can degrade over time when exposed to pure hydrogen, leading to the use of carbon steel pipelines with protective coatings to prevent corrosion. The diameter of these pipelines can vary from 5.1 to 152.4 cm, with operating pressures typically between 0.42 to 0.84 MPa, but in specific cases, it can reach up to 13.9 MPa.

3. Challenges, Opportunities and future prospective

Hydrogen storage technologies emerging have inherent drawbacks and there is yet to be the ideal hydrogen storage method available [60]. Table 5 outlines the challenges and opportunities the hydrogen storage developments are facing. The optimal storage medium should enable high energy densities both volumetrically and gravimetrically, rapid fuel uptake and release, operate under room temperatures and atmospheric pressure, ensure safety during use, and achieve a balanced cost-effectiveness. For future technology to move to mass production, low cost manufacturing process and the safety and maintenance routines and the standards that govern the safe use of the vessels will need improvements for compressed hydrogen storage technology.

Table 5: Summary of opportunities and challenges for hydrogen storage

Challenges	Opportunities
Safety of high operating pressures	Circular economy prospects in structural design
Poor Efficiency	Small/portable storage tanks
Cost challenges	Pipeline blending
Hydrogen embrittlement	Subsea storage
Hydrogen induced cracking and blistering	Repurposed decommissioned oil and gas assets
	Further research into liquefaction boil off prevention
	Further research into improving Hydrogen Embrittlement Relief

3.1 Compressed gas pressure vessels manufacturing Process

The choice of manufacturing process is based on the form and complexity of the product, the tooling and processing costs and the required properties for the product. Filament windings were originally used in pressure vessels production, chemical and water tanks. Before the development of filament winding, dry wire winding of rocket motors was used however this required reinforcement [61]. Several applications are now used in rotor shafts for helicopters, high-pressure pipelines, fuselages for aircrafts, wing sections and all types of structural applications [62].

Filament windings have been the simple base of the manufacturing of pressure vessels however these are the most challenging in terms of design. Pressure vessels with filament winding composites are used for many engineering applications (excluding military) [63]. The filament-winding process is a high-speed procedure in the construction of tubs and various other round components. Filament winding is a technique to produce reinforced composite materials with great resistive properties and it is recognised as cost effective. During the filament winding process the fibre is permeated with resin and wrapped on a mandrel with cylindrical shape [64]. The curing is performed at a specific time and temperature as the speed of the horizontal carrier controls the fibre orientation [62]. Although the mandrel can be part of the design the wound composite is removed from after curing. In summary, fibre reinforced composites are developed using renewable polymer for a starting point, as it has exceptional characteristics preferred in engineering applications because of the low cost, high strength, and low environmental impact [65]. Reinforced composite wrappers are considered to provide the strength to nearly all the cylinders [10].

3.2 Materials, design and manufacturing

While compressed natural gas storage is a well-established technology, it is widely acknowledged that no single hydrogen storage method fully meets all the criteria set by

manufacturers and end-users. Enhancements are required in areas such as weight, storage volume efficiency, conformable shapes, system integration, and cost reduction to fulfill these criteria. Consequently, new design methodologies must focus on delivering a higher strength-to-weight ratio and optimized safe structures, high integrity and reliability, improved manufacturing process monitoring, smart fault detection and versatile shapes (e.g. above 35MPa). Further, the development of maintenance routines and standards for the safe use of the cylinders have not kept pace with the advancement in the carbon fibre compressed cylinder storage technology.

In high-pressure applications, vessels rated at 5,000 psi (34.47 MPa) or higher, categorized as Type III and Type IV vessels, are the most feasible choice. Incorporating high fatigue resistant fiber reinforced composite materials significantly enhances a pressure vessel's corrosion resistance, overall safety, and service life (extending up to approximately 30 years). However, this improvement comes at a higher cost. Lately, the filament windings have been found to be most favoured. However, designing the pressure vessels using such method is difficult, slow and remains expensive due to sophisticated manufacturing and quality assurance. Therefore, there is a need to develop low-cost mass production methods or more reliable hydrogen tanks capable of meeting future demand

The design of hydrogen gas compressors can be difficult due to the ability of hydrogen to degrade materials (hydrogen embrittlement and high temperature hydrogen attack). Hydrogen embrittlement is a phenomenon where hydrogen penetrates into metal, resulting in reduced ductility and tensile strength, causing mechanical damage to the material. It causes brittle fractures; these cracks are always intergranular. Certain metals are more susceptible to embrittlement than others, such as high strength materials. It is assumed that Hydrogen embrittlement is caused by hydrogen atoms when they don't combine fully into hydrogen molecules [66]. There are two types of hydrogen embrittlement, internal which is a result of pre-existing hydrogen already inside the metal, and the second is hydrogen environmental embrittlement, where hydrogen is from the environment.

For liquid hydrogen to be stored at the critical low temperatures a number of considerations are required: to the changes in the mechanical characteristics, expansion and contraction phenomena and the thermal conduction of various materials. Metallic materials in general decrease in ductility and toughness when the temperature is lowered. When it comes to steels, the toughness drops drastically in a narrow temperature range and becomes brittle.

The Charpy impact test is utilized to assess the brittleness of materials under cold temperatures [67]. The testing method involves breaking materials with a U-shaped notch in the centre, and the absorbed energy is calculated by measuring the strength. Tests are conducted at different temperature settings, including submerging the test piece in a bath to lower the temperature. For critical temperatures of liquid hydrogen, insulation is required for the test piece, and the temperature rise during impact testing must be monitored. It should be noted that hydrogen embrittlement susceptibility can only be detected in slow strain tests and not through Charpy impact testing.

Literature suggests that as the temperature decreases, the crystallinity rises, impacting about 50% of the surface at the transition temperature and 100% within the brittleness range [68]. Additional concerns at low temperatures involve potential cold transmission by unaffected metal parts, like stainless steel contraction. To mitigate these issues, appropriate insulation is required to minimize thermal conductivity and account for specific heat at low temperatures.

Liquid hydrogen offers advantages over gaseous form, as highlighted by [27], stating that transportation of hydrogen is more cost-effective in its liquid state. Boil-off during storage, transportation, and handling of liquid hydrogen can consume up to 40% of its available combustion energy. Spherical designs experience a significant decrease in boil-off rate as the tank size increases, while cylindrical tanks with a constant diameter do not show substantial decreases in evaporation rate with size. NASA has developed an integrated refrigeration and storage method for space travel, demonstrating the ability to maintain liquid hydrogen with zero boil-off indefinitely [26].

3.3 Structural integrity due to structural impact failure

Composite materials have become essential for large pressure vessels, but they are vulnerable to damage from impact loading due to their relatively low toughness. A common safety concern in composite overwrapped pressure vessels (COPVs) is the failure caused by low-velocity impacts during operation, repair, and other processes, compromising vessel integrity and leading to hazardous situations. This impact damage can be seen as delamination or cuts in the overwrap or cracks in the resin. There are two different levels of impact damage recognized notably Level 1 and Level 3 [69]. Level 1 damage is only a slight damage, where a very small area where the fibre glass is frosted and can be serviced. Whereas level 3 damage causes a large area of delamination of fibres, frosting or other such structural damage requiring the cylinder to be replaced. Impact testing is utilized to examine dynamic disfigurement and failure methods of materials. Low-velocity affect systems can be characterized as plate-on-plate, pole on-plate, plate-on rod, or on the other hand pole on-pole tests. Two kinds of plate-on-plate affect tests have been produced: wave generation tests and thin-layer high-strain-rate tests. The plate-on-plate tests are additionally characterized as non- recovery or recuperation tests.



Figure 7: Composite tube after burst failure testing, (Source: [59])

Khan and Kim (2011) provided a summary of the continuous research endeavours aimed at enhancing the resistance of composite structures to impact damage, with a specific focus on mitigating delamination effects [70]. Olsson explained that broadly, the loading experienced by composites can be categorized into low-velocity impacts and high-velocity impacts [71]. The type of impact plays a crucial role in the initiation, propagation, and overall effects of

damage. According to Lloyd and Knight, the most critical damage mode affecting the burst strength of COPVs is fiber damage, while damage caused by delamination does not significantly impact the burst pressure [72]. Matemilola and Stronge conducted research on thick epoxy/graphite COPVs, specifically focusing on impact-induced damages [73]. They found that surface fiber damage, particularly in pressure vessels with hoop winding on the outer layer, is the main contributing factor leading to a decline in the burst strength of the pressure vessel.

Drop weight impact test is the most common test for composite materials [74]. Studies show that the damage resulted from the drop weight tests is divided into clearly visible impact damage and the barely visible impact damage. To perform the test, a mass is released from the desired height, to impact the sample, where the machine can be non-instrumented or instrumented. The spread of damage caused by repetitive low-velocity impact (drop-weight or ballistic impact) is severe issue in many composite materials [75]. Furthermore, several impacts may occur during the fabrication, maintenance processes and operation. Also, damage from the low-velocity impact is not easily detected by naked eye. The study on impact-related issues highlights that the primary cause of the decline in burst strength in thick graphite/epoxy composite vessels is external fiber damage, especially in pressure vessels with hoop winding on the outer layer, due to impact-related issues [62][76]. Further investigation into the effects of impactor shape, size, and internal pressure revealed that the key factor leading to reduced burst pressure is fiber damage within the hoop layers. Additionally, it was determined that compressive stress-induced buckling is responsible for the occurrence of fiber damage.

Low-velocity and reduced energy impact tests were conducted on CFRP circular laminated plates to investigate the impact of sampling dimensions and boundary constraints on dynamic behaviour and material damages [77]. Two different diameters and constraints were studied. Numerical simulations of the impact response using a finite element program were compared to experimental results [78]. The examinations revealed that both dimensions and boundary conditions significantly influenced the response and damages, with greater target stiffness resulting in better energy absorption and more extensive delamination [63].

COPVs can experience various types of low-velocity impacts during their production, operation, and maintenance processes. Consequently, assessing the residual burst pressure becomes crucial to ensure the safety of composite overwrapped pressure vessels (COPVs). It is essential to consider the impact damage results during the design phase and develop an efficient analysis system to anticipate both the impact damage and the recurring burst stress of COPVs [79]. In a study involving graphite/epoxy bent cylindrical panels, an impact machine capable of measuring load was used to impact the centre of the panels. Load, deflection, and stress were measured over time for six symmetrical lay-up configurations, using impact forces ranging from 0.5 to 4.5 ft-lb. Damages were observed in all panels at specific impact forces. The extent and location of the damages were determined through C-scans and optical microscopy of panel samples. Random samples indicated that both delamination and transverse splitting contributed to internal damage.

To predict panel deflections and stresses, an internal nonlinear finite element code was employed. The analysis yielded accurate results in predicting the deflection of [0/90] 3s panels and indicated the presence of transverse failure stresses in the central area of the panel. The deflections indicated that the panel boundary exhibited characteristics between simple supported and clamped conditions, with satisfactory agreement achieved when considering hinged support at each edge [80]. Work studied damage model to investigate the intraluminal damages [81]. The Hashin criteria were used to predict composite damage, and the cohesive area model considered delamination. The initial damage significantly reduced the rigidity of the cylinder, and the damage gradually spread until reaching the time of maximum deflection. Moreover, as the impact force increased, the contact time also increased..

Composite tanks for hydrogen storage have also been found by [19] as an extensive application in the oil and gas industry as they exhibit excellent fatigue characteristics and good resistance at extreme temperatures and wear. These composite tanks have been tailored to meet specific application which has its greater advantages such as high axial strength and stiffness, low thermal conductivity and low coefficient of thermal expansion.

A numerical analysis was conducted for Type III tanks, which is a filament wound pressure vessel which is overwrapped with metal liners having plastic behaviour was presented by [82]. The results from this research showed that there is a remarkable drop in the principal axis by the metallic liner in both hoop and helical wound layers of the fibre epoxy composite. Alternative studies focused on the possible variations in winding angles and predicted the behaviour of filament wound structures which included continuous change of fibre angles over the dome area by three-dimensional finite element methods [83]. The experimental results obtained by the strain gages fixed to the outer side of the tank matched the FE results. In the study focused on creating a new generation of filament-wound composite pressure vessels, incorporating a high-density polyethylene liner and thermosetting resin as the matrix, researchers identified failures in specific cross-ply internal layers [84]. Numerical analyses were also conducted on Type IV tanks, revealing that modifying the hoop winding angle in various sections could lead to an approximate 5% reduction in composite usage [85]. The studies also indicated that the required composite weight to meet design requirements increases with the amount of stored hydrogen. Implementing an end cap was found to reduce the thickness of the helical layers, resulting in approximately 10% reduction in composite weight.

Additionally, the study focuses on a thermo-mechanical model of Type IV hydrogen high-pressure storage vessels, investigating the effects of dome thickness, thermal dependencies of mechanical and thermal properties, and damage analysis. The research analyses the vessel's behaviour, considering the influence of damage and temperature through isothermal calculations at different temperature levels [86]. The study observed variations in stress distribution when considering temperature gradients, with the insulation liner being affected by increasing temperatures.

Furthermore, the behaviour of composite pressure vessels made from linear low-density polyethylene (LLDPE) and high-density polyethylene (HDPE) under burst testing was investigated [87]. Based on burst pressure, a combination of finite element analysis and

experimental methods determined the required vessel thickness and appropriate stacking sequences. However, SEM analysis revealed that the composite maintained its dimensional integrity fully [88].

3.4 Standards and regulations of structural design

Unlike natural gas there are currently not many standards and regulations for the structural design of gaseous hydrogen storage tanks. There are a number of standards from storage, transportation and general hydrogen developments published by ISO (International Standards Organisation), CGA (Compressed gas association), NFPA (National Fire prevention association), ASME (American society of mechanical engineers), ANSI (American national standards institute), SAC (State standardisation administration of the P.R.C), CEN (European Committee for standardisation) and JISC (Japanese industrial standards committee) as seen in table 6 [34]. These cover general design and safety, receptacles, pipelines and hydrogen embrittlement. There are significantly more standards surrounding hydrogen embrittlement than any other aspects of hydrogen storage vessels.

Initial inspections and testing are completed at the time of manufacturer and is the responsibility of the manufacturing organisation to comply with the applicable design standards. This process is conducted under the supervision of a notified body chosen by the manufacturer. Pre-fill inspections take place at dedicated filling centers, where skilled personnel follow appropriate procedures using specialized equipment. After the initial inspection is successfully completed, cylinders are authorized for filling and transportation according to the specified period outlined in the inspection protocols.

A series of impact experiments or drop tests need to be performed to test the ability of vessels to withstand internal and external loads, as in the Standard EN 14427 [89]. Additionally, the ISO 1119-3 covers the construction of the composites gas cylinders, in part three of this standard specification of the cylinders and the test methods such burst test and drop test are listed; EN 12245 standard is applicable for the transportation of the fully wrapped composite cylinders and can be employed for both numerically (using advanced 3D FE modelling) [90] and experiments for the low-velocity impact of the pressure vessel (filament wound) vessels manufactured by winding glass fibre with vinyl ester resin over polyethylene liner [89]. The ISO 11439: 2013 standard focuses on cylinder types I, II, III and IV, accounting for the high pressure when storing natural gas for automotive vehicles. Moreover, the standard includes the cylinders made of steel (except for stainless), aluminium alloy or even non-metallic cylinders, different designs for a specific servicing condition (ISO 11439:2013 2018).

Table 6: Snapshot of ISO and BS Standards status in 2023

Brief overview of ISO and BS Standards available and under development in 2023				
Number of Standards	Title	Status	Review	Source
EN 10229:2000	Evaluation of resistance of steel products to hydrogen induced cracking	Published	Under review in 2023/5	[91]
EN ISO 11114-4: 2017	Transportable gas cylinders - Compatibility of cylinder and valve materials with gas contents - Part 4: Test methods for selecting steels resistant to hydrogen embrittlement	Published	Under review in 2023	[91]
EN ISO 15330: 1999	Fasteners - Preloading test for the detection of hydrogen embrittlement – parallel bearing surface method	Published	Reviewed in 2012	[91]
ISO 10587:2000	Metallic and other inorganic coatings - Test for residual embrittlement in both metallic coated and uncoated externally threaded articles and rods - Inclined wedge method	Published	Under review in 2025	[91]
ISO 11114-4:2017	Transportable gas cylinders - Compatibility of cylinder and valve materials with gas contents - Part 4: Test methods for selecting steels resistant to hydrogen embrittlement	Published	Under review in 2023	[91]
ISO 11623:2015	Gas cylinders — Composite construction — Periodic inspection and testing	Published	Will be replaced by ISO/FDIS 11623	[91]
ISO 15330:1999	Fasteners - Preloading test for the detection of hydrogen embrittlement – parallel bearing surface method	Published	Reviewed in 2017	[91]
ISO 16111:2018	Transportable gas storage devices – hydrogen absorbed in reversible metal hydride	Published	Under review in 2023	[91]
ISO 16573-1:2020	Steel — Measurement method for the evaluation of hydrogen embrittlement	Published	Under review in 2025	[91]

	resistance of high strength steels — Part 1: constant load test			
ISO 19881:2018	Gaseous hydrogen — Land vehicle fuel containers	Published	Will be replaced by ISO/AWI 19881	[91]
ISO 24431:2016	Gas cylinders — Seamless, welded and composite cylinders for compressed and liquefied gases (excluding acetylene) — Inspection at time of filling	Published	Reviewed in 2022	[91]
ISO 2626:1973	Copper – Hydrogen embrittlement test	Published	Reviewed in 2019	[91]
ISO 7539-11:2013	Corrosion of metals and alloys - Stress corrosion testing – Part 11: Guidelines for testing the resistance of metals and alloys to hydrogen embrittlement and hydrogen-assisted cracking	Published	Reviewed in 2018	[91]
ISO 9587:2007	Metallic and other inorganic coatings - Pre-treatment of iron or steel to reduce the risk of hydrogen embrittlement	Published	Will be replaced by ISO/WD 24251-1	[91]
ISO 9588:2007	Metallic and other inorganic coatings - Post-coating treatments of iron or steel to reduce the risk of hydrogen embrittlement	Published	Will be replaced by ISO/WD 24251-1	[91]
ISO/AWI 19881	Gaseous hydrogen — Land vehicle fuel containers	Under Development		[91]
ISO/AWI TR 15916	Basic considerations for the safety of hydrogen systems	Under Development		[91]
ISO/AWI TR 19884-2	Gaseous Hydrogen - Cylinders and tubes for stationary storage — Part 2: Material test data of class A materials (steels and aluminium alloys) compatible to hydrogen service	Under Development		[91]
ISO/AWI TR 19884-3	Gaseous Hydrogen - Cylinders and tubes for stationary storage — Part 3: Pressure cycle test data to	Under Development		[91]

	demonstrate shallow pressure cycle estimation methods			
ISO/CD 19884-1	Gaseous hydrogen — Cylinders and tubes for stationary storage — Part 1: General Requirements	Under Development		[91]
ISO/FDIS 11623	Gas cylinders — Composite cylinders and tubes — Periodic inspection and testing	Under Development		[91]
ISO/TR 15916:2015	Basic considerations for the safety of hydrogen systems	Published	Will be replaced by ISO/AWI TR 15916	[91]
ISO/TR 20491:2019	Fasteners - Fundamentals of hydrogen embrittlement in steel fasteners	Published	Under review in 2024	[91]
ISO/TS 10839:2022	Polyethylene pipes and fittings for the supply of gaseous fuels — code of practice for design, handling and installation	Published	Under review in 2027	[91]
ISO/WD 24251-1	Prevention of hydrogen assisted brittle fracture of high-strength steel components — Part 1: Fundamentals and measures	Under Development		[91]
BS EN 17533:2020	Gaseous hydrogen. Cylinders and tubes for stationary storage	Published	Under review in 2025	[90]
BS EN 2831:1993	Hydrogen embrittlement of steels. Test by slow bending	Published		[90]
BS EN 2832:1993	Hydrogen embrittlement of steels. Notched specimen test	Published		[90]
BS ISO 14687:2019	Hydrogen fuel quality. Product specification	Published	Under review in 2024	[90]
BS ISO 26142:2010	Hydrogen detection apparatus. Stationary applications	Published		[90]

3.5 Safety risks due Operational to high pressure

It is recommended that high operating pressures should be limited to -235°C , operating pressures should be limited to values less than 5MPa for cryogenic temperatures or elevated temperatures (up to -235°C) [92]. Operating pressure should be reduced to 35MPa for room temperature applications. With higher pressure comes higher safety risks, and the safety of these pressurised cylinders can be a concern in highly populated areas. Highly pressurised hydrogen does not react well with oxygen at ambient pressures and temperatures, causing unwanted reactions and ignition. With the increased pressure, the likelihood of leaks is higher, and the ranges of flammability widen. Hydrogen gas is odourless therefore sensors are required to detect leakages. The safety of the high operating pressures has also been linked to the wide flammability and sensitivity to ignition and detonation [93].

The rupture of the laminate leads to the burst effect on a composite tank, where the internal pressure and extra loads predominate. The most critical failure mechanism in burst effect is the rupture of the laminate [94]. One of the main issues which a composite pressure vessel can face is the risk of hydrogen embrittlement of steel due to the premature crack. It can occur because of the hydrogen atoms dissolution and trap. Consequently, the risk of the burst of the vessels is high [15].

Researchers developed a specific continuum damage mechanics model to simulate the burst behaviour of hyperbaric pressure vessels, utilizing the fixed damage directions approach [95]. This model links the damage directions to the composite orthotropic axes through tensorial functions representation theory. Moreover, the same methodology allowed for the prediction of burst pressure and pressure mode in Type IV pressure vessels [95].

Additionally, they conducted experiments to analyse the burst failure of filament wound pressure vessels made of T-800 graphite/epoxy. By using a degenerated finite shell element that considered the winding angle variation and thickness along the meridional line of the cylinder, they successfully predicted the vessel's damage propagation under applied load. The experimental burst pressure measurement aligned with the theoretical approach [96].

3.6 Subsea storage and pipeline blending

The use of large hydrogen storage systems submerged underwater has the potential to address the gap between renewable energy production and intermittent energy supply. There is a significant demand for large-scale storage methods suitable for pure hydrogen, and the utilization of composite materials offers the possibility of storing substantial amounts of hydrogen for varying durations. Submerging the composite vessels below sea level allow energy storage close or even connected to the renewable energy source powering electrolysis. Subsea storage solutions allow for the efficiency and pressure of the tank to be adapted with the different depths of the water.

The blending hydrogen into the natural gas pipeline network presents an opportunity to advance the adoption of hydrogen as a clean energy source worldwide [97]. However, this approach also brings challenges, notably in material selection for future pipelines, due to hydrogen embrittlement in the current steel pipeline network, which hinders the increase in the ratio of natural gas to hydrogen [98]. There is an opportunity for demonstration projects

of large-scale hydrogen pipelines at high pressures as already existing steel pipeline networks may already suffer from stress corrosion, poor quality welds and mechanical damage, making the conditions unsuitable for hydrogen. There is also an opportunity to investigate the behaviour of the varied concentrations of hydrogen-methane mixture under different conditions, such as high/low pressure and temperature [99].

3.7 Efficiency, cost and circular economy prospects in structural design

It is suggested in the DOE Hydrogen and fuel Cell Record that there is yet to be a method of energy conversion step, from production, storage, and utilization [100]. The energy required to compress hydrogen to 700 bar and deliver it to a vehicle can vary from 5% to 20% of the hydrogen's lower heating value, while PEM fuel cells achieve an efficiency of around 60%. It is suggested that hydrogen demands almost as much energy to produce as it delivers, with an efficiency percentage of approximately 60%. Nevertheless, hydrogen can efficiently store large amounts, increasing its density.

The cost of large-scale storage vessels is a topic of significant discussion, with particular attention on the expenses arising from the substantial amount of robust materials necessary for the structure [101]. Currently, researchers are actively involved in developing cost-effective carbon fiber solutions that can meet the essential stress, strain, and safety criteria for high-pressure storage tanks. The key to successful implementation lies in adhering to thickness limitations for the tank to achieve the desired volumetric capacity objectives. Literature proves that a circular approach has been taken on board in a number of hydrogen storage systems, with the reuse of underground hydrocarbon storage and the repurposing of buried pipelines to ensure suitability for hydrogen [102]. However, there is little to no literature on the end of life for hydrogen storage. Designing products for end-of-life scenarios is vital to facilitate material recovery and reuse, aiming to minimise waste generation. [103].

4. Conclusion

With the increasing demand for hydrogen, it is important that large scale storage develops. The literature shows that there are numerous types of underground storage methods to store hydrogen. Adapting previous underground gas storage systems, has the lowest costs due to the lack of exploration and construction needed. However, manmade salt caverns allow for a significantly higher number of cycles of removing hydrogen a year, allowing for seasonal storage. Salt caverns are also a popular choice within Europe, with the UK storing 1million m³ of pure hydrogen. In terms of surface hydrogen storage, the use of liquified hydrogen is the store and transport in cryogenic tanks, however there are issues with evaporation rates.

In conclusion, existing literature has highlighted the significant impact of composite damages on the behaviour and residual strength of composite pressure vessels. These damages, including fiber and matrix fractures, as well as delamination, should be duly considered in impact examinations. The enhancement of glass fibres to composite material increases the tensile strength, chemical resistance and insulating properties of the composite pressure vessel as well as also the addition of polymer-based resins raises toughness as well as tightness to the composite pressure vessel. There are many issues demonstrated within the literature for hydrogen storage, one main one being hydrogen embrittlement of storage

vessel materials. This becomes more of an issue with the use of cryogenic tanks due to the low temperatures affecting the ductility and toughness of the metallic materials.

References

1.

PETRONE G. Composite Panels in Transportation Engineering. 2009; Available from: http://www.superpanels.unina.it/SUPERPANELS/Deliverables_files/DWP1-2.pdf

2.

Varney C. Hydrogen East [Internet]. 2021. (www.hydrogeneast.uk). Available from: <https://hydrogeneast.uk/government-to-go-above-and-beyond-for-hydrogen-and-net-zero/>

3.

Niaz S, Manzoor T, Pandith AH. Hydrogen storage: Materials, methods and perspectives. 2015 Oct;50:457–69. Available from: <https://dx.doi.org/10.1016/j.rser.2015.05.011>

4.

Azeem M, Ya HH, Alam MA, Kumar M, Stabla P, Smolnicki M, et al. Application of Filament Winding Technology in Composite Pressure Vessels and Challenges: A Review. 2022 May;49:103468. Available from: <https://dx.doi.org/10.1016/j.est.2021.103468>

5.

Ciancia A, Pede G, Brighigna M, Perrone V. Compressed hydrogen fuelled vehicles: Reasons of a choice and developments in ENEA. 1996;21(5):397–406. Available from: [https://dx.doi.org/10.1016/0360-3199\(95\)00093-3](https://dx.doi.org/10.1016/0360-3199(95)00093-3)

6.

Ramirez JP, Halm D, Grandidier J-C, Villalonga S. A fixed directions damage model for composite materials dedicated to hyperbaric type IV hydrogen storage vessel – Part I: Model

formulation and identification. 2015 Oct 15;40(38):13165–73. Available from:
<https://dx.doi.org/10.1016/j.ijhydene.2014.08.071>

7.

Yanxing Z, Maoqiong G, Yuan Z, Xueqiang D, Jun S. Thermodynamics analysis of hydrogen storage based on compressed gaseous hydrogen, liquid hydrogen and cryo-compressed hydrogen. 2019 Jun 21;44(31):16833–40. Available from:
<https://dx.doi.org/10.1016/j.ijhydene.2019.04.207>

8.

Notardonato WU, Swanger AM, Fesmire JE, Jumper KM, Johnson WL, Tomsik TM. Zero boil-off methods for large-scale liquid hydrogen tanks using integrated refrigeration and storage. 2017 Dec 1;278(1):12012. Available from: <https://iopscience.iop.org/article/10.1088/1757-899X/278/1/012012>

9.

Ball M, Wietschel M. The hydrogen economy: Opportunities and challenges [Internet]. Cambridge University Press, Cambridge; 2009. 4 p. Available from:
<http://publica.fraunhofer.de/documents/N-110223.html>

10.

Dhakal H., Skrifvars M, Adekunle K, Zhang Z. Falling weight impact response of jute/methacrylated soybean oil bio-composites under low velocity impact loading. 2014 Feb 24;92:134–41. Available from: <https://dx.doi.org/10.1016/j.compscitech.2013.12.014>

11.

Mazumdar SK. Composites Manufacturing: Materials, Products, and Process Engineering. 2010;4(1):86. Available from: <https://search.proquest.com/docview/195251901>

12.

krishnamurthy T, Muralidhar I. Fabrication of Low Cost Filament Winding Machine. 2014;1(4):30–9.

13.

Wang H, Tong Z, Zhou G, Zhang C, Zhou H, Wang Y, et al. Research and demonstration on hydrogen compatibility of pipelines: a review of current status and challenges. 2022 Aug 1;47(66):28585–604. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2022.06.158>

14.

Razavi Setvati M, Mustaffa Z, Shafiq N, Syed ZI. A Review on Composite Materials for Offshore Structures. In American Society of Mechanical Engineers; 2014. (Volume 5: Materials Technology; Petroleum Technology). Available from:
<https://asmedigitalcollection.asme.org/OMAE/proceedings/OMAE2014/45455/San%20Francisco,%20California,%20USA/269620>

15.

Palazotto A, Perry R, Sandhu R. Impact response of graphite/epoxy cylindrical panels. 1992 Jul;30(7):1827–32. Available from: <http://arc.aiaa.org/doi/full/10.2514/3.11143>

16.

Ahluwalia R., Hua T., Peng J-K, Lasher S, McKenney K, Sinha J, et al. Technical assessment of cryo-compressed hydrogen storage tank systems for automotive applications. 2010;35(9):4171–84. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2010.02.074>

17.

Li Y, Yang RT. Significantly Enhanced Hydrogen Storage in Metal–Organic Frameworks via Spillover. 2006 Jan 25;128(3):726–7. Available from: <http://dx.doi.org/10.1021/ja056831s>

18.

Jafari Raad SM, Leonenko Y, Hassanzadeh H. Hydrogen storage in saline aquifers: Opportunities and challenges. 2022 Oct;168:112846. Available from: <https://dx.doi.org/10.1016/j.rser.2022.112846>

19.

Rivard E, Trudeau M, Zaghbi K. Hydrogen Storage for Mobility: A Review. 2019 Jun 19;12(12):1973. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/31248099>

20.

Matemilola SA, Stronge WJ. Low-Speed Impact Damage in Filament-Wound CFRP Composite Pressure Vessels. 1997 Nov 1;119(4):435–43. Available from: <http://dx.doi.org/10.1115/1.2842327>

21.

Davids M., Lototsky M, Malinowski M, van Schalkwyk D, Parsons A, Pasupathi S, et al. Metal hydride hydrogen storage tank for light fuel cell vehicle. 2019 Nov 8;44(55):29263–72. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2019.01.227>

22.

Tarkowski R. Underground hydrogen storage: Characteristics and prospects. 2019 May;105:86–94. Available from: <https://dx.doi.org/10.1016/j.rser.2019.01.051>

23.

Gentilleau B, Touchard F, Grandidier J. Numerical study of influence of temperature and matrix cracking on type IV hydrogen high pressure storage vessel behavior. 2014 May;111:98–110. Available from: <https://dx.doi.org/10.1016/j.compstruct.2013.12.034>

24.

Murakami Y. 21 - Hydrogen embrittlement [Internet]. Murakami Y, editor. Academic Press; 2019 [cited 2022 Jan 12]. 41 p. (Metal Fatigue (Second Edition)). Available from: <https://www.sciencedirect.com/science/article/pii/B9780128138762000212>

25.

Mahajan D, Tan K, Venkatesh T, Kileti P, Clayton CR. Hydrogen Blending in Gas Pipeline Networks—A Review. 2022 May 13;15(10):3582. Available from: <https://search.proquest.com/docview/2670145823>

26.

Felderhoff M, Weidenthaler C, von Helmolt R, Eberle U. Hydrogen storage: the remaining scientific and technological challenges. 2007 May 23;9(21):2643–53. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/17627309>

27.

Olsson R. Impact response of orthotropic composite plates predicted from a one-parameter differential equation. 1992 Jun;30(6):1587–96. Available from: <http://arc.aiaa.org/doi/full/10.2514/3.11105>

28.

Duell J. Impact Testing of Advanced Composites. 2004;97–112.

29.

Azeem M, Ya HH, Alam MA, Kumar M, Stabla P, Smolnicki M, et al. Application of Filament Winding Technology in Composite Pressure Vessels and Challenges: A Review. 2022 May;49:103468. Available from: <https://dx.doi.org/10.1016/j.est.2021.103468>

30.

Barthelemy H. Hydrogen storage – Industrial prospectives. 2012 Nov;37(22):17364–72. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2012.04.121>

31.

Fu Q. The Entirely Optimal Design of the Lightweight High-pressure Hydrogen Storage Vessel. Zhejiang University; 2004.

32.

Paster MD, Ahluwalia RK, Berry G, Elgowainy A, Lasher S, McKenney K, et al. Hydrogen storage technology options for fuel cell vehicles: Well-to-wheel costs, energy efficiencies, and greenhouse gas emissions. 2011;36(22):14534–51.

33.

Lloyd B, KNIGHT G. Impact damage sensitivity of filament-wound composite pressure vessels. In 1986. (Impact damage sensitivity of filament-wound composite pressure vessels). Available from: <https://search.proquest.com/docview/24109268>

34.

Züttel A, Schlapbach L. Hydrogen-storage materials for mobile applications. 2001 Nov 15;414(6861):353–8. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/11713542>

35.

Xin SH, Wen HM. A progressive damage model for fiber reinforced plastic composites subjected to impact loading. 2015 Jan;75:40–52. Available from: <https://dx.doi.org/10.1016/j.ijimpeng.2014.07.014>

36.

SOUAHLIA A, DHAOU H, MELLOULI S, ASKRI F, JEMNI A, BEN NASRALLAH S. Experimental study of metal hydride-based hydrogen storage tank at constant supply pressure. 2014;39(14):7365–72.

37.

Barthelemy H, Weber M, Barbier F. Hydrogen storage: Recent improvements and industrial perspectives. 2017 Mar 16;42(11):7254–62. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2016.03.178>

38.

Zivar D, Kumar S, Foroozesh J. Underground hydrogen storage: A comprehensive review. 2021 Jul 1;46(45):23436–62. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2020.08.138>

39.

Crotogino F. Larger Scale Hydrogen Storage. 2016. 19 p. (Storing Energy : With Special Reference to Renewable Energy Sources).

40.

Allevi C, Collodi G. 12 - Hydrogen production in IGCC systems [Internet]. Elsevier Ltd; 2017. 25 p. (Integrated Gasification Combined Cycle (IGCC) Technologies). Available from: <https://dx.doi.org/10.1016/B978-0-08-100167-7.00012-3>

41.

Barboza Neto E., Chludzinski M, Roese P., Fonseca JS., Amico S., Ferreira C. Experimental and numerical analysis of a LLDPE/HDPE liner for a composite pressure vessel. 2011 Sep;30(6):693–700. Available from: <https://dx.doi.org/10.1016/j.polymertesting.2011.04.016>

42.

Simbeck D, Chang E. Hydrogen Supply: Cost Estimate for Hydrogen Pathways--Scoping Analysis, January 22, 2002--July 22, 2002 [Internet]. United States; 2002 Nov. Available from: <https://www.osti.gov/servlets/purl/15002482>

43.

Papavinasam S. Chapter 5 - Mechanisms [Internet]. Papavinasam S, editor. Boston: Gulf Professional Publishing; 2014 [cited 2022 Jan 11]. 52 p. (Corrosion Control in the Oil and Gas Industry). Available from:

<https://www.sciencedirect.com/science/article/pii/B9780123970220000054>

44.

Luxfer. Luxfer Carbon Composite Cylinders Inspection Manual 2009 [Internet]. 2009.

Available from:

https://www.luxfercylinders.com/img/rm_img/blog_img/454/attachments/1/luxcompinspect_manual.pdf

45.

Park J-S, Hong C-S, Kim C-G, Kim C-U. Analysis of filament wound composite structures considering the change of winding angles through the thickness direction. 2002;55(1):63–71.

Available from: [https://dx.doi.org/10.1016/S0263-8223\(01\)00137-4](https://dx.doi.org/10.1016/S0263-8223(01)00137-4)

46.

Dutta S. A review on production, storage of hydrogen and its utilization as an energy resource. 2014 Jul 25;20(4):1148–56. Available from:

<https://dx.doi.org/10.1016/j.jiec.2013.07.037>

47.

Pimm A, Garvey SD. Chapter 7 - Underwater Compressed Air Energy Storage [Internet].

Elsevier Inc; 2016. 20 p. (Storing Energy). Available from: <https://dx.doi.org/10.1016/B978-0-12-803440-8.00007-5>

48.

Murthy S, Kumar A. Advanced materials for solid state hydrogen storage: “Thermal engineering issues.” 2014 Nov 22;72(2):176–89. Available from:

<https://dx.doi.org/10.1016/j.applthermaleng.2014.04.020>

49.

Lankof L, Tarkowski R. Assessment of the potential for underground hydrogen storage in bedded salt formation. 2020 Jul 31;45(38):19479–92. Available from:

<https://dx.doi.org/10.1016/j.ijhydene.2020.05.024>

50.

Valenti G. 2 - Hydrogen liquefaction and liquid hydrogen storage [Internet]. Elsevier Ltd; 2016. 25 p. (Compendium of Hydrogen Energy). Available from:

<https://dx.doi.org/10.1016/B978-1-78242-362-1.00002-X>

51.

Hübner F, Brückner A, Dickhut T, Altstädt V, Rios de Anda A, Ruckdäschel H. Low temperature fatigue crack propagation in toughened epoxy resins aimed for filament winding of type V

composite pressure vessels. 2021 Oct;102:107323. Available from:
<https://dx.doi.org/10.1016/j.polymertesting.2021.107323>

52.

Kabir MZ. Finite element analysis of composite pressure vessels with a load sharing metallic liner. 2000;49(3):247–55. Available from: [https://dx.doi.org/10.1016/S0263-8223\(99\)00044-6](https://dx.doi.org/10.1016/S0263-8223(99)00044-6)

53.

Berthelot JM. Dynamics of Composites and structures
. 2008.

54.

ZHANG Y, JIA Z, YUAN Z, YANG T, QI Y, ZHAO D. Development and Application of Hydrogen Storage. 2015;22(9):757–70. Available from:
<http://lib.cqvip.com/qk/86787X/201509/666566760.html>

55.

Sarkar A, Banerjee R. Net energy analysis of hydrogen storage options. 2005;30(8):867–77. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2004.10.021>

56.

Heinemann N, Alcalde J, Miodic JM, Hangx SJT, Kallmeyer J, Ostertag-Henning C, et al. Enabling large-scale hydrogen storage in porous media - the scientific challenges. 2021 Feb 23;14(2):853–64.

57.

MUTASHER S, NASIRI NM-, LIN LC. SMALL-SCALE FILAMENT WINDING MACHINE FOR PRODUCING FIBER COMPOSITE PRODUCTS. 2012 Apr 1;7(2):156–68. Available from:
<https://doaj.org/article/f3ca450793ea4c7384a0f5f217f2f5ac>

58.

Judd R, Pinchbeck D. 8 - Hydrogen admixture to the natural gas grid [Internet]. Elsevier Ltd; 2016. 28 p. (Compendium of Hydrogen Energy). Available from:
<https://dx.doi.org/10.1016/B978-1-78242-364-5.00008-7>

59.

Onder A, Sayman O, Dogan T, Tarakcioglu N. Burst failure load of composite pressure vessels. 2009;89(1):159–66. Available from: <https://dx.doi.org/10.1016/j.compstruct.2008.06.021>

60.

Perillo G, Grytten F, Sørbo S, Delhaye V. Numerical/experimental impact events on filament wound composite pressure vessel. 2015 Feb;69:406–17. Available from:
<https://dx.doi.org/10.1016/j.compositesb.2014.10.030>

61.

BSI. British Standards Institution (BSI) [Internet]. 2023. Available from: <https://www.bsigroup.com/en-GB/standards/>

62.

Barral K, Barthelemy H. Hydrogen high pressure tanks storages: overview and new trends due to H2 Energy specifications and constraints. 2006.

63.

Doh YD, Hong CS. Progressive Failure Analysis for Filament Wound Pressure Vessel. 1995 Dec;14(12):1278–306. Available from: <https://journals.sagepub.com/doi/full/10.1177/073168449501401203>

64.

Reuß M, Grube T, Robinius M, Preuster P, Wasserscheid P, Stolten D. Seasonal storage and alternative carriers: A flexible hydrogen supply chain model. 2017 Aug 15;200:290–302. Available from: <https://dx.doi.org/10.1016/j.apenergy.2017.05.050>

65.

Zheng J, Liu X, Xu P, Liu P, Zhao Y, Yang J. Development of high pressure gaseous hydrogen storage technologies. 2012;37(1):1048–57. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2011.02.125>

66.

Antonia O, Penev M. Blending hydrogen into natural gas pipeline networks [Internet]. Golden, Colorado: National Renewable Energy Laboratory; 2013. (NREL/TP). Available from: <https://purl.fdlp.gov/GPO/gpo41640>

67.

Williams J., Silverman S. Composites Technology Used Onshore With Synergy to Offshore Applications. In Offshore Technology Conference; 1999. Available from: <https://www.onepetro.org/conference-paper/OTC-11062-MS>

68.

Di Profio P, Arca S, Rossi F, Filippini M. Comparison of hydrogen hydrates with existing hydrogen storage technologies: Energetic and economic evaluations. 2009;34(22):9173–80. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2009.09.056>

69.

Xiao J, Hu M, Bénard P, Chahine R. Simulation of hydrogen storage tank packed with metal-organic framework. 2013 Sep 30;38(29):13000–10. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2013.03.140>

70.

Celia M, Bachu S, Nordbotten J, Bandilla K. Status of CO₂ storage in deep saline aquifers with emphasis on modeling approaches and practical simulations. 2015;51(9).

71.

Zittel A. Hydrogen storage methods. 2004 Apr;91(4):157–72. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/15085273>

72.

Azeem M, Ya HH, Alam MA, Kumar M, Stabla P, Smolnicki M, et al. Application of Filament Winding Technology in Composite Pressure Vessels and Challenges: A Review. 2022 May;49:103468. Available from: <https://dx.doi.org/10.1016/j.est.2021.103468>

73.

Yáñez M, Ortiz A, Brunaud B, Grossmann I., Ortiz I. The use of optimization tools for the Hydrogen Circular Economy [Internet]. Elsevier; 2019. 6 p. (Computer Aided Chemical Engineering; vol. 46). Available from: <https://dx.doi.org/10.1016/B978-0-12-818634-3.50297-6>

74.

Pentimalli M, Padella F, La Barbera A, Piloni L, Imperi E. A metal hydride–polymer composite for hydrogen storage applications. 2009;50(12):3140–6. Available from: <https://dx.doi.org/10.1016/j.enconman.2009.08.021>

75.

Mouti Z, Westwood K, Long D, Njuguna J. An experimental investigation into localised low-velocity impact loading on glass fibre-reinforced polyamide automotive product. 2013 Oct;104:43–53. Available from: <https://dx.doi.org/10.1016/j.compstruct.2013.03.014>

76.

Caglayan DG, Weber N, Heinrichs HU, Linßen J, Robinius M, Kukla PA, et al. Technical potential of salt caverns for hydrogen storage in Europe. 2020 Feb 28;45(11):6793–805. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2019.12.161>

77.

Cheng SZD, Jin S. Chapter 5 Crystallization and melting of metastable crystalline polymers [Internet]. 2002. 29 p. (Handbook of Thermal Analysis and Calorimetry; vol. 3). Available from: [https://dx.doi.org/10.1016/S1573-4374\(02\)80008-5](https://dx.doi.org/10.1016/S1573-4374(02)80008-5)

78.

Echtermeyer AT, Lasn K. Safety approach for composite pressure vessels for road transport of hydrogen. Part 2: Safety factors and test requirements. 2014 Sep 3;39(26):14142–52. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2014.06.016>

79.

Sherif S., Zeytinoglu N, Veziroğlu T. Liquid hydrogen: Potential, problems, and a proposed research program. 1997;22(7):683–8. Available from: [https://dx.doi.org/10.1016/S0360-3199\(96\)00201-7](https://dx.doi.org/10.1016/S0360-3199(96)00201-7)

80.

Muhammed NS, Haq MB, Al Shehri DA, Al-Ahmed A, Rahman MM, Zaman E, et al. Hydrogen storage in depleted gas reservoirs: A comprehensive review. 2023 Apr 1;337:127032. Available from: <https://dx.doi.org/10.1016/j.fuel.2022.127032>

81.

ISO. International Organization for Standardization (ISO) [Internet]. 2023. Available from: <https://www.iso.org>

82.

Richardson MO., Wisheart M. Review of low-velocity impact properties of composite materials. 1996;27(12):1123–31. Available from: [https://dx.doi.org/10.1016/1359-835X\(96\)00074-7](https://dx.doi.org/10.1016/1359-835X(96)00074-7)

83.

Andersson J, Grönkvist S. Large-scale storage of hydrogen. 2019 May 3;44(23):11901–19. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2019.03.063>

84.

Bünger U, Michalski J, Crotogino F, Kruck O. 7 - Large-scale underground storage of hydrogen for the grid integration of renewable energy and other applications [Internet]. Elsevier Ltd; 2016. 31 p. (Compendium of Hydrogen Energy). Available from: <https://dx.doi.org/10.1016/B978-1-78242-364-5.00007-5>

85.

Bellosta von Colbe J, Ares J-R, Barale J, Baricco M, Buckley C, Capurso G, et al. Application of hydrides in hydrogen storage and compression: Achievements, outlook and perspectives. 2019 Mar 22;44(15):7780–808. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2019.01.104>

86.

Gardiner M. DOE Hydrogen and Fuel Cells Program Record. 2009.

87.

Rivard E, Trudeau M, Zaghib K. Hydrogen Storage for Mobility: A Review. 2019 Jun 19;12(12):1973. Available from: <https://www.ncbi.nlm.nih.gov/pubmed/31248099>

88.

Institute HR. Materials-for-End-to-End-Hydrogen_Roadmap. 2021.

89.

Raza A, Arif M, Glatz G, Mahmoud M, Al Kobaisi M, Alafnan S, et al. A holistic overview of underground hydrogen storage: Influencing factors, current understanding, and outlook. 2022 Dec 15;330:125636. Available from: <https://dx.doi.org/10.1016/j.fuel.2022.125636>

90.

Hirscher M, Yartys VA, Baricco M, Bellosta von Colbe J, Blanchard D, Jr B RC., et al. Materials for hydrogen-based energy storage – past, recent progress and future outlook. 2020;827. Available from: <http://hdl.handle.net/2078.1/231507>

91.

Fan J, Njuguna J. An introduction to lightweight composite materials and their use in transport structures [Internet]. Elsevier Ltd; 2016. 32 p. (Lightweight Composite Structures in Transport). Available from: <https://dx.doi.org/10.1016/B978-1-78242-325-6.00001-3>

92.

Matemilola SA, Stronge WJ. Low-Speed Impact Damage in Filament-Wound CFRP Composite Pressure Vessels. 1997 Nov 1;119(4):435–43. Available from: <http://dx.doi.org/10.1115/1.2842327>

93.

Ng HD, Lee JHS. Comments on explosion problems for hydrogen safety. 2008;21(2):136–46. Available from: <https://dx.doi.org/10.1016/j.jlp.2007.06.001>

94.

Ye Y, Lu J, Ding J, Wang W, Yan J. Numerical simulation on the storage performance of a phase change materials based metal hydride hydrogen storage tank. 2020 Nov 15;278:115682. Available from: <https://dx.doi.org/10.1016/j.apenergy.2020.115682>

95.

Johansson F, Spross J, Damasceno D, Johansson J, Stille H. Investigation of research needs regarding the storage of hydrogen gas in lined rock caverns [Internet]. 2018. (TRITA-ABE-RPT). Available from: <http://urn.kb.se/resolve?urn=urn:nbn:se:kth:diva-231034>

96.

Moradi R, Groth KM. Hydrogen storage and delivery: Review of the state of the art technologies and risk and reliability analysis. 2019 May 3;44(23):12254–69. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2019.03.041>

97.

Khan SU, Kim J-K. Impact and Delamination Failure of Multiscale Carbon Nanotube-Fiber Reinforced Polymer Composites: A Review. 2011 Jun 30;12(2):115–33. Available from:

<https://www.kci.go.kr/kciportal/ci/sereArticleSearch/ciSereArtiView.kci?sereArticleSearchBean.artid=ART001739036>

98.

IEA. World Energy Investment 2022 - WorldEnergyInvestment2022.pdf. 2022 [cited 2023 May 15]; Available from: <https://iea.blob.core.windows.net/assets/b0beda65-8a1d-46ae-87a2-f95947ec2714/WorldEnergyInvestment2022.pdf>

99.

Landinger H, Bungler U, Raksha T, Weindorf W, Simon J, Correias L, et al. HyUnder - Benchmarking of large scale hydrogen underground storage with competing options. 2014; Available from: http://hyunder.eu/wp-content/uploads/2016/01/D2.2_Benchmarking-of-large-scale-seasonal-hydrogen-underground-storage-with-competing-options_final.pdf

100.

Grid N. Hydrogen: the future fuel to achieve net zero? [Internet]. 2022. (www.nationalgrid.com). Available from: <https://www.nationalgrid.com/stories/journey-to-net-zero-stories/hydrogen-future-fuel-achieve-net-zero>

101.

Elberry AM, Thakur J, Santasalo-Aarnio A, Larmi M. Large-scale compressed hydrogen storage as part of renewable electricity storage systems. 2021 Apr 26;46(29):15671–90. Available from: <https://dx.doi.org/10.1016/j.ijhydene.2021.02.080>

102.

Kostopoulos V, Kotrotsos A, Geitona A, Tsantzalis S. Low velocity impact response and post impact assessment of carbon fiber/epoxy composites modified with Diels-Alder based healing agent. A novel approach. 2021 Jan;140:106151. Available from: <https://dx.doi.org/10.1016/j.compositesa.2020.106151>

103.

Velosa J., Nunes J., Antunes P., Silva J., Marques A. Development of a new generation of filament wound composite pressure cylinders. 2009;69(9):1348–53. Available from: <https://dx.doi.org/10.1016/j.compscitech.2008.09.018>