



## OpenAIR@RGU

### The Open Access Institutional Repository at Robert Gordon University

<http://openair.rgu.ac.uk>

This is the published version of a paper in

Energy and Environment Research (ISSN 1927-0569, eISSN 1927-0577)
---

#### Citation Details

##### Citation for the version of the work held in 'OpenAIR@RGU':

KAJAMA, M.N., NWOGU, N.C. and GOBINA, E., 2014. Gas permeation study using porous ceramic membranes. Available from <i>OpenAIR@RGU</i> . [online]. Available from: <a href="http://openair.rgu.ac.uk">http://openair.rgu.ac.uk</a>
--

##### Citation for the publisher's version:

KAJAMA, M.N., NWOGU, N.C. and GOBINA, E., 2014. Gas permeation study using porous ceramic membranes. <i>Energy and Environment Research</i> , Vol 4 (3), pp. 43-49.
---



This work is licensed under a  
[Creative Commons Attribution 3.0 Unported License](https://creativecommons.org/licenses/by/3.0/).

#### Copyright

Items in 'OpenAIR@RGU', Robert Gordon University Open Access Institutional Repository, are protected by copyright and intellectual property law. If you believe that any material held in 'OpenAIR@RGU' infringes copyright, please contact [openair-help@rgu.ac.uk](mailto:openair-help@rgu.ac.uk) with details. The item will be removed from the repository while the claim is investigated.

DOI: <http://dx.doi.org/10.5539/eer.v4n3p43>

# Gas Permeation Study Using Porous Ceramic Membranes

Mohammed N. Kajama<sup>1</sup>, Ngozi C. Nwogu<sup>1</sup> & Edward Gobina<sup>1</sup>

<sup>1</sup> Centre for Process Integration and Membrane Technology (CPIMT), IDEAS Research Institute, School of Engineering, The Robert Gordon University, Aberdeen, AB10 7GJ, United Kingdom

Correspondence: Professor Edward Gobina, Centre for Process Integration and Membrane Technology, School of Engineering, The Robert Gordon University, Riverside East, Garthdee Road, Aberdeen, AB10 7GJ, United Kingdom. Tel: 44-(0)1224-26-2348. Fax: 44-(0)1224-26-2444. E-mail: e.gobina@rgu.ac.uk

Received: June 12, 2014 Accepted: July 9, 2014 Online Published: July 11, 2014

doi:10.5539/eer.v4n3p43

URL: <http://dx.doi.org/10.5539/eer.v4n3p43>

## Abstract

A 6000 nm ceramic membrane was repaired with boehmite solution (ALOOH) through the repeat dip-coating technique. The permeance of hydrogen (H<sub>2</sub>) and carbon dioxide (CO<sub>2</sub>) were obtained through the membrane in relation to average pressure at room temperature for the support membrane and as cracked membrane. A repair process was carried out on the cracked membrane by same dip coating process and results obtained after first and second dips. The permeance of the support membrane obtained ranged between  $1.50$  to  $3.04 \times 10^{-7} \text{ mol m}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$ . However, as a result of a crack that occurred during the removal of the membrane from the reactor, the permeance increased from  $2.96$  to  $5.82 \times 10^{-7} \text{ mol m}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$ . Further application of boehmite solution on the membrane lead to an improvement on the surface of the membrane with some degree and surface cracks were reduced. This also decreased the permeance to  $1.26 - 3.39 \times 10^{-8} \text{ mol m}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$  after the second dip. Consequently, another silica based modified membrane was used for carbon dioxide and nitrogen (N<sub>2</sub>) permeation. The plots show that carbon dioxide permeated faster than the other gases, indicating dominance of a more selective adsorptive transport mechanism. Accordingly, results obtained show an appreciable high carbon dioxide permeance of  $3.42 \times 10^{-6} \text{ mol m}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$  at a relatively low pressure when compared to nitrogen confirming that the membrane has so far exhibited a high permeability, selectivity and high CO<sub>2</sub> gas recovery. The permselectivities of CO<sub>2</sub> over H<sub>2</sub> at room temperature was also obtained which were higher than the Knudsen selectivity.

**Keywords:** ceramic membranes, gas permeation, hydrogen selectivity, carbon dioxide selectivity, defect repair

## 1. Introduction

Carbon dioxide is one of the many greenhouse gases which contribute to global warming. Membrane technology has been suggested as a substitute to the use of conventional separation processes (e.g. dehydration, gas adsorption, distillation among others) due to their unique attributes such as thermal and mechanical stability, as well as harsh chemical resistance (Singh et al., 2004; Anwu et al., 1997). The employment of inorganic membranes in the industry has extended the application of membranes for hydrogen production, CO<sub>2</sub> recovery as well as H<sub>2</sub>S removal from associated gas feed streams because of their simplicity and low energy requirement (Yildirim & Hughes, 2002).

There are several methods for porous membrane modification including; dip-coating, chemical vapour deposition (CVD), and pulsed layer deposition (Pejman et al., 2011; Benito et al., 2005; Koutsonikolas et al., 2010). Out of the mentioned modification methods, dip-coating method has many merits over the other methods such as its simplicity, uniform surface and the ability of controlling the pore structure of the membrane (Pejman et al., 2011). However, a lot of research is still needed to examine membrane modification through dip-coating method in order to elucidate the morphological effects of dip-coated membranes. Membranes defects are formed during preparation stages. It can be formed either during dipping, drying, calcination process and sealing (Koutsonikolas et al., 2010) or even during the process of inserting and removing it from the reactor. Any defect on a macroporous membrane (pore diameter > 50 nm) can be regarded as a crack. For example, a defect is considered in the presence of super-micropores ( $0.7 \text{ nm} < \text{pore diameter} < 2 \text{ nm}$ ) instead of ultra-micropores (pore diameter < 0.7 nm) (Koutsonikolas et al., 2010). It is known that any amount of defect on the membrane can significantly lower the membrane selectivity.

Lambropoulos et al. (2007) repaired  $\gamma$ -alumina and silica membranes at 573 K by CVD process with a tetraethylorthosilicate (TEOS)/O<sub>3</sub> counter reactant configuration. The defect was characterised with a permeability technique and a novel mercury intrusion. However, Gopalakrishnan et al. (2007) applied a hybrid processing method for hydrogen-selective membrane preparation. They applied a primary sol-gel silica layer for the CVD zone thickness reduction, and a CVD modification with tetramethoxysilane (TMOS) and O<sub>2</sub> at 873 K. After which they only examined H<sub>2</sub>/N<sub>2</sub> selectivity to be 2300 at 873 K. Pejman et al. (2011) modified the surface of ceramic supports to facilitate the deposition of defect-free overlying micro and mesoporous membrane. They investigated the effects of dipping time, heating rate, and number of coated layers on microstructure of the modified layers in their study. They have achieved a smoother surface and the cracks size was reduced dramatically after two dip-coating steps.

In this paper, we have repaired a crack on a ceramic membrane with boehmite solution (ALOOH), also carbon dioxide separation and the effects of permeation properties such as; permeation pressure was examined.

## 2. Experimental

The commercial ceramic membrane used was supplied by Ceramiques Techniques et Industrielles (CTI SA) France, consisted of (77%  $\alpha$ -alumina + 23% TiO<sub>2</sub>) with an average pore diameter of 6000 nm. The membrane has 19.8 mm and 25 mm internal and outer diameter respectively, and a permeable length of 318 mm. The feed pressure applied was between 0.05 to 5 bar at room temperature. Figures 1 and 2 show a SEM image of inside and outside surface of the porous ceramic membranes. The membrane's structure was defect-free before the 1<sup>st</sup> dip. An SEM of the cross section of the same membrane is also shown in Figure 3. During the removal of the membrane from the reactor; the membrane was cracked Figure 4 i.e. after gas permeation before modification.

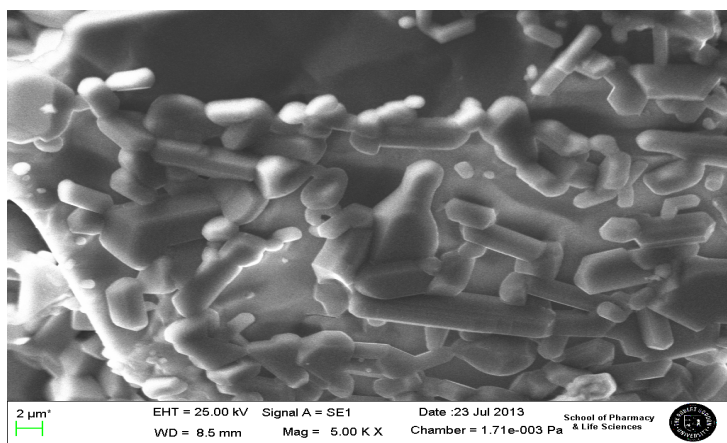


Figure 1. SEM image of the inside surface

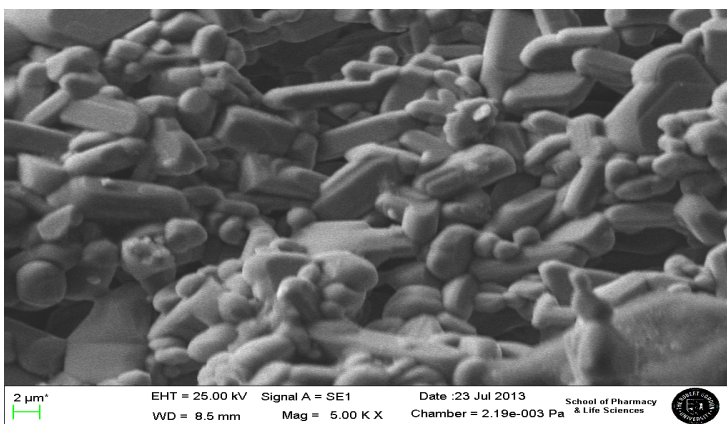


Figure 2. Outside surface of ceramic membrane

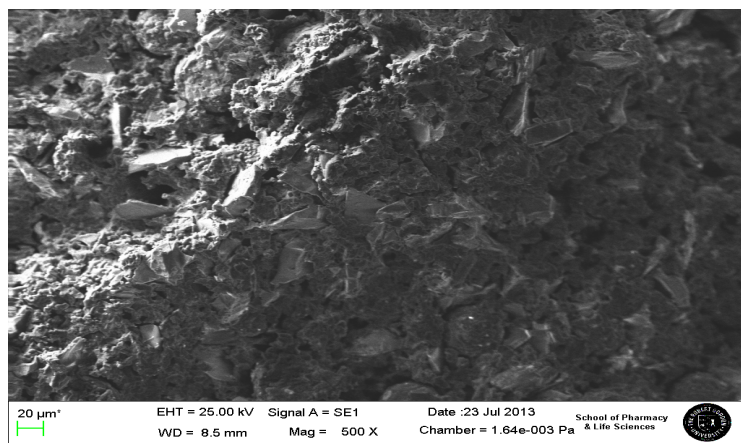


Figure 3. SEM image of the cross section of the membrane

In order to repair the defected surface of the substrate a 36 g/1000 L boehmite sol was used. A dip-coating method was applied to repair the defected membrane. The internal surface of the coarse alumina tube membrane was exposed to boehmite solution for 30 minutes. After this, the membrane was air-dried overnight and then heat-treated using the temperature profile shown in Figure 5. The dipping-drying firing procedure was repeated in order to achieve the required  $\gamma$ -alumina layer on the coarse support. The prepared membrane glazed at each end was sealed within the stainless steel reactor using graphite seals.

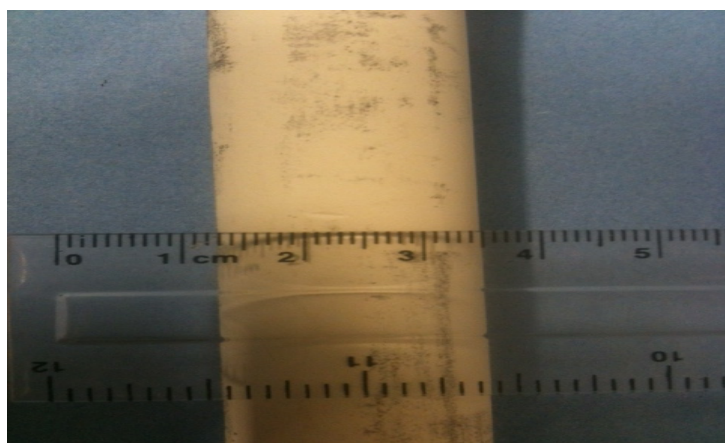


Figure 4. Pictorial view of the cracked membrane

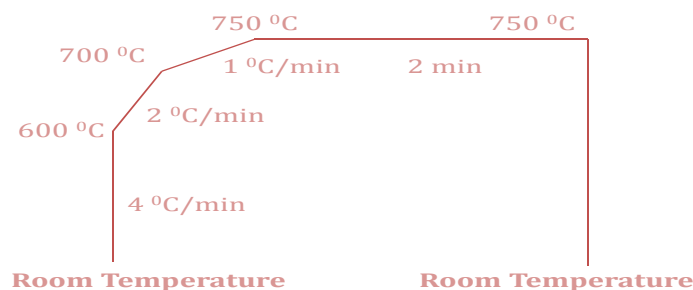


Figure 5. Membrane's heat-treatment profile

Single gas permeation measurements were carried out for gas components ( $H_2$  and  $CO_2$ ) at room temperature using the experimental setup shown in Figure 6 with the retentate valve fully open to the fume cupboard. The

permeate flow tube was connected to the flowmeter to record gas flow rate. Gas permeance was obtained from the following expression;

$$Q = \left( \frac{q}{A \cdot \Delta P} \right) \quad (1)$$

Where  $Q$  is the Permeance ( $\text{mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$ );  $q$  is the molar flow ( $\text{mol/sec}$ );  $A$  is the membrane area ( $\text{m}^2$ ); and  $\Delta P$  is the pressure difference ( $\text{Pa}$ ) across the membrane.



Figure 6. Experimental arrangement for the membrane reactor

The permselectivity of the membrane was also obtained using Equation (2);

$$S_{ij} = Q_i / Q_j \quad (2)$$

Where  $S_{ij}$  is the permselectivity of  $i$  to  $j$ ;  $Q_i$  is the permeance of  $i$  ( $\text{mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$ );  $Q_j$  is the permeance of  $j$  ( $\text{mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$ ).

### 3. Results and Discussion

Figure 7 shows the results of carbon dioxide permeance through the multilayered alumina membrane against average pressure at room temperature for the support membrane, cracked membrane, first and second dip repaired with boehmite solution stages. It can be seen that the permeance of the support is between  $1.50$  to  $3.04 \times 10^{-7} \text{ mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$ . However, due to the crack which occurred during the removal of the membrane from the reactor, the permeance increased to  $2.96 - 5.82 \times 10^{-7} \text{ mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$ . After exposing boehmite solution to the membrane, the surface was improved to some degree, surface cracks are also lowered, and the permeance decreased to  $1.26 - 3.39 \times 10^{-8} \text{ mol m}^{-2} \text{s}^{-1} \text{Pa}^{-1}$  after the second dip which is almost parallel to the x-axis which indicates the applicability of Knudsen diffusion mechanism.

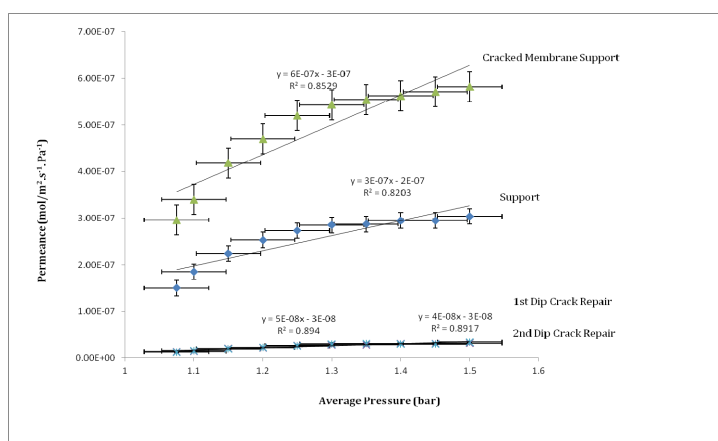


Figure 7. Permeance against average pressure for carbon dioxide at room temperature

Silica layer membrane was also prepared using the repeated dip-coating method (Gobina, 2006) which allows CO<sub>2</sub> to permeate faster from flue gas by maintaining a pressure drop across the membrane due to surface diffusion despite its higher molecular weight. It can be seen in Figure 8 that the graph showing the effect of feed pressure on CO<sub>2</sub> and N<sub>2</sub> permeance. From a feed pressure of about 1.4 bar, the permeance of CO<sub>2</sub> was quite higher than that of N<sub>2</sub>, which indicates the presence of surface diffusion while that of N<sub>2</sub> reduced drastically which indicates the presence of Knudsen diffusion mechanism.

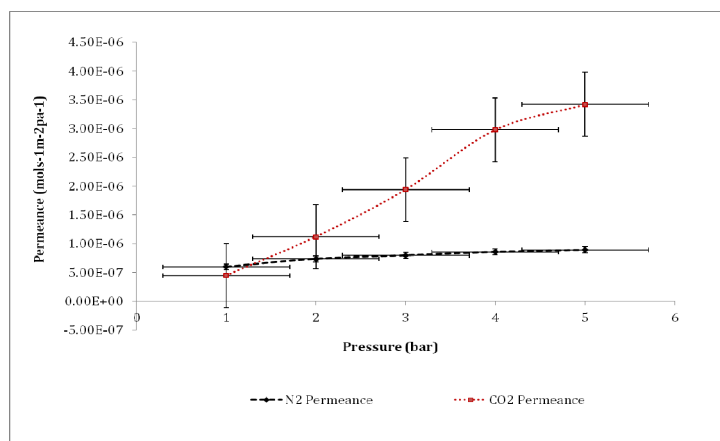


Figure 8. Effect of pressure on CO<sub>2</sub> and N<sub>2</sub> permeance

The permselectivities of CO<sub>2</sub> over H<sub>2</sub> at room temperature is shown in Figure 9. It can be seen that the selectivities obtained are higher than the Knudsen selectivity. After exposing the support to the boehmite solution, it was observed that a significant increase in the selectivity to CO<sub>2</sub> had occurred for the first dip crack repair as shown in Figure 9. Subsequent dips however reduced the CO<sub>2</sub> selectivity. This behaviour is related to the transport regime in the membrane. Transport owing to the combination of diffusion through the gas phase in the pores of the membrane and surface diffusion is a combination of mechanisms. The total transport in the absence of a pressure difference over the membrane of  $i$  owing to the combination of diffusion through the gas phase in the pores of the membrane and surface diffusion is described by Equation (3);

$$J_{i, \text{tot}} = J_{i, \text{gas}} + (4/d_p) J_{i, \text{surf}} \quad (3)$$

Where  $J_{i, \text{tot}}$  = total molar flux owing to both transport mechanisms (mol·m<sup>-2</sup>·s<sup>-1</sup>),  $J_{i, \text{gas}}$  = molar flux owing to transport in the gas phase in the pores (mol·m<sup>-2</sup>·s<sup>-1</sup>), and  $d_p$  = average pore diameter (m).

In the present study, it was assumed that the pores could be regarded as ideally cylindrically shaped although this assumption is questionable for alumina membranes. Another complicating factor is the homogeneity of the distribution of the  $\gamma$ -alumina over the  $\alpha$ -alumina surface inside the membrane. As the main objective of the present study was to demonstrate the occurrence of surface diffusion effects in ceramic membrane reactors no special attention has been paid to the actual pore configuration. Moreover, pore shape only affects the value of the constants of the denominator of the term for  $J_{i, \text{surf}}$  in Equation (3), e.g. rectangular pores have a value of 4. The geometric factor  $4/d_p$  in Equation (3) arises from the fact that transport owing to diffusion through the gas phase in the pores is proportional to the cross-sectional area of the pores, therefore proportional to  $d_p^2$  whereas transport owing to surface diffusion is proportional to the circumference of the pores, therefore proportional to  $d_p$ . The molar flux of component  $i$  through the gas phase in the pores of the membrane is described by Fick's law using the Bosanquet formula for the combination of Knudsen and continuum diffusion by the principle of resistances in series.

It is demonstrated experimentally that during the 1<sup>st</sup> dip repair surface diffusion of CO<sub>2</sub> in an alumina membrane impregnated with  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, can contribute substantially to the transport rate. Moreover, for this system it is of almost the same order of magnitude as the transport caused by ordinary diffusion through the gas phase in the pores. Subsequent dipping result in continuum diffusion and the molar flux is therefore independent of pressure. Surface diffusion however is linearly proportional to the pressure provided the fraction of the adsorption sites covered is very low. It is demonstrated that the resulting difference in pressure dependence of both transport mechanisms can be used to distinguish between diffusion through the gas phase in the pores and surface diffusion.

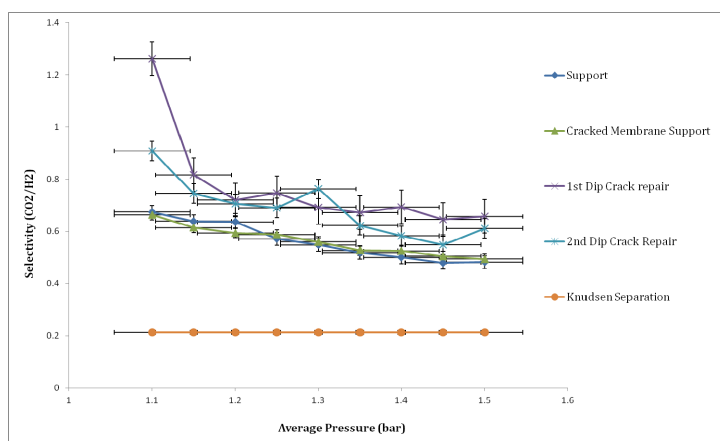


Figure 9. Selectivity of CO<sub>2</sub>/H<sub>2</sub> against average pressure at room temperature

#### 4. Conclusions

A simple but effective technique to modify nanostructure ceramic membranes which involves dip-coating method was studied and involved the use of boehmite solution to modify the membrane. Several parameters such as dipping time, number of coating, heating rate on the nanostructure were investigated. A high temperature heat-treatment was applied in order to repair defects on the commercial membranes, and to improve the permselectivity of these membranes above Knudsen regime selectivity. Single gas permeation tests were used to examine the permeance of the membrane. After the first and second modifications with boehmite solution, permeance decreased significantly which indicates the presence of Knudsen diffusion mechanism.

The silica membrane is thought to exhibit higher CO<sub>2</sub> permeance from flue gas N<sub>2</sub> by maintaining a pressure drop across the membrane due to surface diffusion mechanism. In general, inorganic membranes would exhibit an improved performance on carbon dioxide separation from flue gases.

#### Acknowledgements

The authors gratefully acknowledge Petroleum Technology Development Fund (PTDF) Nigeria for funding this research, and School of pharmacy & Life Sciences RGU for the SEM results.

#### References

- Anwu, L. I., Hongbin, Z., Jinghua, G. U., & Guoxing, X. (1997). Preparation of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> composite membrane and examination of membrane defects. *Science in China (Series B)*, 40(1), 31-36. <http://dx.doi.org/10.1007/BF02882185>
- Benito, J. M., Conesa, A., Rubio, F., & Rodriguez, M. A. (2005). Preparation and characterization of tubular ceramic membranes for treatment of oil emulsions. *Journal of the European Ceramic Society*, 25, 1895-1903. <http://dx.doi.org/10.1016/j.jeurceramsoc.2004.06.016>
- Gobina, E. (2006). Apparatus and Methods for Separating Gases. United States Granted Patent No. US 7048778, May 23, 2006.
- Gopalakrishnan, S., Yoshino, Y., Nomura, M., Nair, B. N., & Nakao, S. I. (2007). A hybrid processing method for high performance hydrogen-selective silica membranes. *Journal of Membrane Science*, 297, 5-9. <http://dx.doi.org/10.1016/j.memsci.2007.03.034>
- Koutsonikolas, D., Kaldis, S., Sakellaropoulos, G. P., Loon, M. H. V., Dirrix, R. W. J., & Terpstra, R. A. (2010). Defects in microporous silica membranes: Analysis and repair. *Separation and Purification Technology*, 73, 20-24. <http://dx.doi.org/10.1016/j.seppur.2009.07.027>
- Lambropoulos, A., Romanos, G., Steriotis, Th., Nolan, J., Katsaros, F., Kouvelos, E., ... Kanellopoulos, N. (2007). Application of an innovative mercury intrusion technique and relative permeability to examine the thin layer pores of sol-gel and CVD post-treated membranes. *Microporous and Mesoporous Materials*, 99, 206-215. <http://dx.doi.org/10.1016/j.micromeso.2006.08.038>
- Pejman, A. N., Akbar, B. A., Elham, J., Majid, P., & Masoumeh, A. A. (2011). An optimum routine for surface modification of ceramic supports to facilitate deposition of defect-free overlaying micro and meso (nano) porous membrane. *Iran. J. Chem. Eng.*, 30(3), 63-73.

- Singh, R. P., Way, J. D., & McCarley, K. C. (2004). Development of a model surface flow membrane by modification of porous Vycor glass with a fluorosilane. *Ind. Eng. Chem. Res*, 43, 3033-3040. <http://dx.doi.org/10.1021/ie030679q>
- Yildirim, Y., & Hughes, R. (2002). The efficient combustion of O-xylene in a Knudsen controlled catalytic membrane reactor. *Trans IChemE*, 80(Part B), 159-164. <http://dx.doi.org/10.1205/095758202317576265>

### Copyrights

Copyright for this article is retained by the author(s), with first publication rights granted to the journal.

This is an open-access article distributed under the terms and conditions of the Creative Commons Attribution license (<http://creativecommons.org/licenses/by/3.0/>).