

RUTTKAY-NEDECKÝ, B., DOČEKALOVÁ, M., HOSNEDLOVÁ, B., UHLÍŘOVÁ, D., STAŇKOVÁ, M., KEPINSKA, M., MILNEROWICZ, H., FERNANDEZ, C., BAROŇ, M., SOCHOR, J., NGUYEN, H.V. and KIZEK, R. 2018. Antioxidant activity of silver nanoparticles prepared by green synthesis. In Proceedings of 10th Nanomaterials international conference 2018 (NANOCON 2018): research and application, 17-19 October 2018, Brno, Czech Republic. Ostrava: Tanger Ltd [online], pages 392-396. Available from: <https://www.confer.cz/nanocon/2018/download/189-antioxidant-activity-of-silver-nanoparticles-prepared-by-green-synthesis.pdf>

# Antioxidant activity of silver nanoparticles prepared by green synthesis.

RUTTKAY-NEDECKÝ, B., DOČEKALOVÁ, M., HOSNEDLOVÁ, B., UHLÍŘOVÁ, D., STAŇKOVÁ, M., KEPINSKA, M., MILNEROWICZ, H., FERNANDEZ, C., BAROŇ, M., SOCHOR, J., NGUYEN, H.V., KIZEK, R.

2018



## ANTIOXIDANT ACTIVITY OF SILVER NANOPARTICLES PREPARED BY GREEN SYNTHESIS

<sup>1</sup>Branislav RUTTKAY-NEDECKÝ, <sup>2</sup>Michaela DOČEKALOVÁ, <sup>3</sup>Božena HOSNEDLOVÁ, <sup>2</sup>Dagmar UHLÍŘOVÁ, <sup>2</sup>Martina STAŇKOVÁ, <sup>4</sup>Marta KEPINSKA, <sup>4</sup>Halina MILNEROWICZ, <sup>5</sup>Carlos FERNANDEZ, <sup>3</sup>Mojmír BAROŇ, <sup>3</sup>Jiří SOCHOR, <sup>6</sup>Hoai Viet NGUYEN, Rene KIZEK <sup>1,2,4</sup>

<sup>1</sup>University of Veterinary and Pharmaceutical Sciences Brno, Pharmaceutical Faculty, Brno, Czech Republic, EU, [kizek@sci.muni.cz](mailto:kizek@sci.muni.cz)

<sup>2</sup>Prevention Medicals, Studenka-Butovice, Czech Republic, EU, [uhlirova@preventionmedicals.cz](mailto:uhlirova@preventionmedicals.cz)

<sup>3</sup>Mendel University in Brno, Faculty of Horticulture, Department of Viticulture and Enology, Lednice, Czech Republic, EU, [sochor.jirik@seznam.cz](mailto:sochor.jirik@seznam.cz)

<sup>4</sup>Department of Biomedical and Environmental Analyses, Faculty of Pharmacy with Division of Laboratory Diagnostics, Wroclaw Medical University, Wroclaw, Poland, EU, [zalewska.m@gmail.com](mailto:zalewska.m@gmail.com)

<sup>5</sup>Robert Gordon University, School of Pharmacy and Life Sciences Garthdee Road, Aberdeen, AB10 7QB, Scotland, United Kingdom; [c.fernandez@rgu.ac.uk](mailto:c.fernandez@rgu.ac.uk)

<sup>6</sup>Research Center for Environmental Monitoring and Modeling, VNU University of Science, Hanoi, Vietnam, [nguyenviethoai@hus.edu.vn](mailto:nguyenviethoai@hus.edu.vn)

### Abstract

At present, great attention is given to silver nanoparticles (AgNPs), which thanks to its unique properties, such as good electric conductivity, photoelectrochemical activity and antimicrobial activity are widely used. Green synthesis of nanoparticles uses biological molecules from living organisms. Biological extracts may contain molecules which exhibit significant antibacterial, antiviral and cytotoxic effects. The aim of this work was to study the diverse AgNPs synthesized from 10 different types of plant extracts. Extracts from dried plants (0.5 g/25 mL 18 MΩ water) were prepared at 70 ° C by heating for 20 minutes. After filtration, the leachates were mixed in the 1:1 ratio with 0.1 M AgNO<sub>3</sub> and allowed to stir at room temperature for 18 hours. They were then mixed in the 1:1 ratio with methanol, shaken for 5 minutes on the rotary mixer, and centrifuged at 12,000 g for 30 minutes. After removing the supernatant, the pellet was dried at 60°C for 24 hours. After weighing, the purified AgNPs were dissolved in 18 MΩ of water. AgNPs were yellow, orange and brown. The extraction efficiency was monitored by organic solvents (methanol, ethanol, acetone, propanol). The yields of AgNPs ranged from 15 to 5%, and the most suitable solvent was methanol with an average AgNPs yield of about 10%. AgNPs were characterized spectrally (spectral maxima were in the range of 300-500 nm) by determining the zeta potential and the size of nanoparticles (30-80 nm). Furthermore, antioxidant activity was monitored using ABTS (670 nm), DPPH (517 nm), and FRAP (595 nm) methods. Two methods (ABTS and DPPH) based on the elimination of synthetic radicals and the FRAP method based on the reduction of iron complexes were used to monitor the antioxidant activity. Antioxidation assays were evaluated using calibration curve equations in which the standard was gallic acid. The results for the ABTS and DPPH methods were also expressed as percentage of inhibition of the radicals and in the FRAP method as percentage of reduction activity. The results were calculated using the ABTS method in the range (25.9 -84.9%), in the DPPH method (19.2-86.6%) and in the FRAP method (8.5 --93.2%). Most AgNPs prepared by green synthesis showed significant antioxidant activity.

**Keywords:** Nanomedicine, silver nanoparticles, green synthesis, antioxidant activity

## 1. INTRODUCTION

The synthesis of silver nanoparticles (AgNPs) attracts an increasing interest due to their new and different characteristics that allow applications in various fields such as antimicrobials, anticancer agents medicine and biotechnology[1]. AgNPs have properties of high surface area, very small size and high dispersion, and are one of the most commonly used nanomaterials. AgNPs are known to have also antioxidant properties[2]. Several techniques have demonstrated that AgNPs can be synthesized using chemical and physical methods, but due to the fact of usage of a huge amount of toxic chemicals and high temperature conditions, a search for alternative method began. Synthesis of nanoparticles by biological methods, using microorganisms, enzyme and plant or plant extract, has been suggested as possible eco-friendly alternatives to chemical and physical methods[3]. The use of plant extracts to produce nanoparticles is one of environmental friendly green processes. Nanoparticles produced from plant extract, because of their medicinal properties, could be used in drugs, targeted drug delivery and cosmetic applications [4]. The various biomolecules present in the plant extract such as enzymes, proteins, flavonoids, terpenoids, and cofactors act as both reducing and capping agents[5]. The plant-mediated synthesis of nanoparticles is relatively fast as there is no need of maintaining specific media and culture conditions, unlike microbial synthesis[5].

Most of the oxidative diseases are due to oxidative stress resulting from free radicals[6]. Free radicals such as superoxide anion, hydroxyl radicals and non-radical species such as hydrogen peroxide and singlet oxygen are different varieties of activated oxygen constituting reactive oxygen species[7]. An active antioxidative defense system is needed to balance the output of free radicals. Antioxidant therapy by the curing of these diseases has an enormous importance. Nanotechnology is an interdisciplinary approach in biochemical applications and focusing on synthesis of nanoparticles have improved antimicrobial and antioxidant properties against the degenerative diseases and cancer[8]. Antioxidant activity in plant extract is due to the redox potential of phytochemicals[9], which can play an important role in quenching singlet and triplet oxygen, decomposing the peroxides or neutralizing the free radicals. Therefore, it is assumed that higher antioxidant activity of nanoparticles might be due to the preferential adsorption of the antioxidant material from the plant extract onto the surface of the nanoparticles. In our study we used ten types of greenly synthesized AgNPs from medicinal plants or food of plant origin and we tested them for their antioxidant activity using DPPH, ABTS and FRAP methods.

## 2. MATERIAL AND METHODS

### 2.1 Nanoparticle synthesis

10 different plants were used for preparation of AgNPs extracts. The plants were the following: AgNPs 1 – black tea (*Camelia sinensis*), AgNPs 2 – green tea (*Camelia sinensis*), AgNPs 3 - coffee (*Coffea Arabica*), AgNPs 4 – common thyme (*Thymus vulgaris*), AgNPs 5 – red clover (*Trifolium pratense*), AgNPs 6 – red raspberry (*Rubus idaeus*), AgNPs 7 – absinthe wormwood (*Artemisia absinthium*), AgNPs 8 – common agrimony (*Agrimonia eupatoria*), AgNPs 9 – garden strawberry (*Fragaria ananassa*), AgNPs 10 – purple crownvetch (*Securigera varia*). Extracts from dried plants (0.5 g/25 mL 18 MΩ water) were prepared at 70 ° C by heating for 20 minutes. After filtration, the leachates were mixed in the 1:1 ratio with 0.1 M AgNO<sub>3</sub> and allowed to stir at room temperature for 18 hours. The prepared AgNPs solution was stored at 4 ° C in closed containers and spectrally characterized. AgNPs solutions were also used for the determination of antioxidant activity.

### 2.2 Characterization of nanoparticles

The absorbance spectra of nanoparticles were recorded within the range from 350 to 700 nm using an UV-3100PC UV-VIS spectrophotometer (VWR, Germany).


### 2.3 Antioxidant properties of nanoparticles

Photometric measurements were carried out using an automated chemical analyser BS-300 (Mindray, China). For detection itself, the following range of wavelengths can be used - 340, 380, 412, 450, 505, 546, 570, 605, 660, 700, 740 and 800 nm. The DPPH test is based on the ability of the stable 2, 2-diphenyl-1-picrylhydrazyl (DPPH) free radical to react with hydrogen donors. A 150  $\mu\text{L}$  volume of reagent (0.095 mM 2,2-diphenyl-1-picrylhydrazyl - DPPH $\bullet$ ) was incubated with 15  $\mu\text{L}$  of sample. Absorbance was measured at 505 nm for 12 minutes and output ratio was achieved by difference of absorbance at the last (12th) minute and second minute of the assay procedure. The ABTS radical method is one of the most used assays for the determination of the concentration of free radicals. It is based on the neutralization of a radical-cation arising from the one-electron oxidation of the synthetic chromophore 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulfonic acid) (ABTS):  $\text{ABTS}\bullet - e^- \rightarrow \text{ABTS}\bullet+$ . This reaction is monitored spectrophotometrically by the change of the absorption value. A 150  $\mu\text{L}$  volume of reagent 7mM ABTS $\bullet$  (2,2'-azinobis 3-ethylbenzothiazoline-6-sulfonic acid and 4.95 mM potassium peroxodisulphate) is poured with 3  $\mu\text{L}$  of sample. Absorbance is measured at 660 nm. To calculate the antioxidant activity, difference between absorbance at the last (12th) minute and second minute of the assay procedure was used. The FRAP method (Ferric Reducing Antioxidant Power) is based on the reduction of complexes of 2,4,6-tripyridyl-s-triazine (TPTZ) with ferric chloride hexahydrate ( $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ ), which are almost colourless, and eventually slightly brownish. This chemical forms blue ferrous complexes after its reduction. Reagent preparation: Solution 1: 10  $\text{mmol}\cdot\text{L}^{-1}$  solution of TPTZ in 40  $\text{mmol}\cdot\text{L}^{-1}$  of hydrochloric acid. Solution 2: 20  $\text{mmol}\cdot\text{L}^{-1}$  solution of ferric chloride hexahydrate in ACS water. Solution 3: 20  $\text{mmol}\cdot\text{L}^{-1}$  acetate buffer, pH 3.6. These three solutions (TPTZ,  $\text{FeCl}_3$ , acetate buffer) are mixed in a 1:1:10 ratio. A 150  $\mu\text{L}$  volume of reagent is injected into a plastic cuvette with subsequent addition of a 3  $\mu\text{L}$  sample. Absorbance is measured at 605 nm for 12 minutes. Difference between absorbance at the last (12th) minute and second minute of the assay procedure was used for calculating of the antioxidant activity.

## 3. RESULTS

### 3.1 Characterization of nanoparticles


The AgNPs were characterized by absorbance spectra (Fig. 1, A, B, C, D, E, F, G, H, I, J-a) with the three characteristic absorption maxima that ranged between 220 -230 nm, 270-290 nm and 470-480 nm (AgNPs B) (Fig. 1, A-J-a). Fig. 1, A – J-b illustrates the relevant images of the AgNPs prepared by green synthesis.

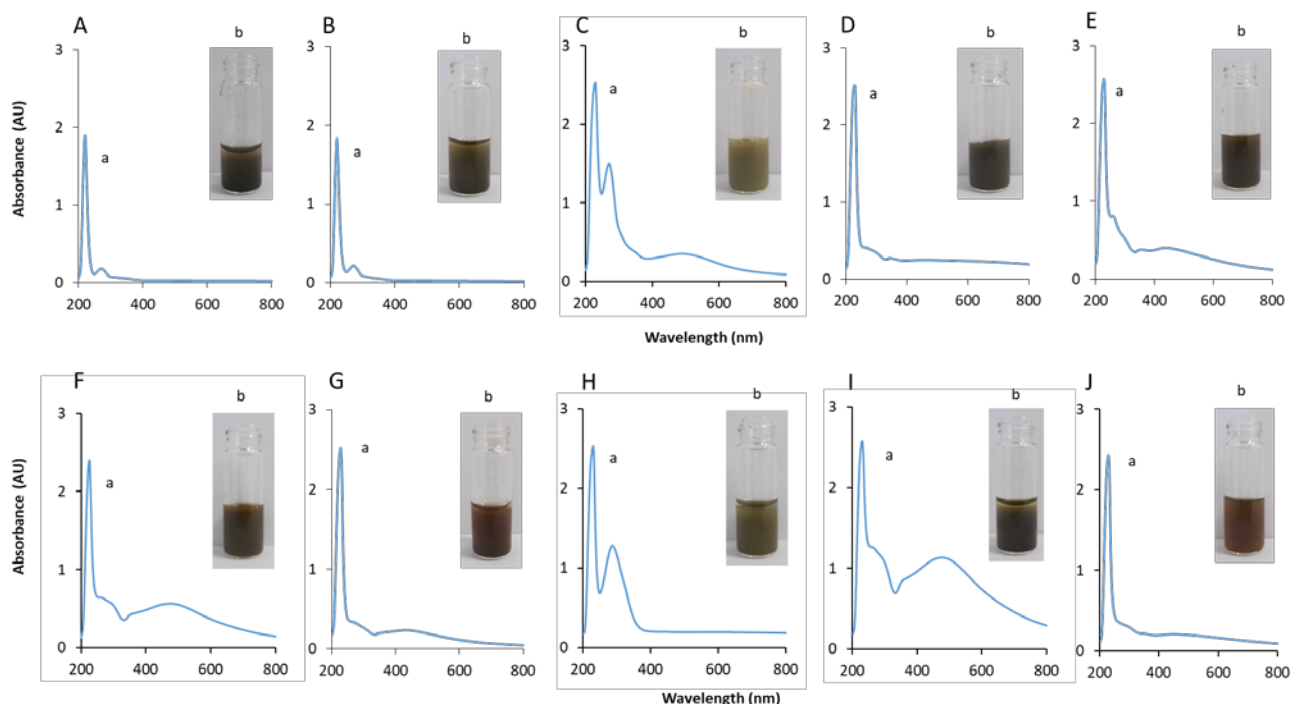

**Fig.1** Characterization of AgNPs synthesized by green synthesis (A - AgNPs 1, B - AgNPs 2, C – AgNPs 3, D- AgNPs – 4, E – AgNPs – 5, F – AgNPs 6, G - AgNPs 7, H – AgNPs 8, I – AgNPs 9, J – AgNPs 10). AgNPs were prepared using following plant extracts: : AgNPs 1 – black tea (*Camelia sinensis*), AgNPs 2 – green tea (*Camelia sinensis*), AgNPs 3 - coffee (*Coffea Arabica*), AgNPs 4 – common thyme (*Thymus vulgaris*), AgNPs 5 – red clover (*Trifolium pratense*), AgNPs 6 – red raspberry (*Rubus idaeus*), AgNPs 7 – absinthe wormwood (*Artemisia absinthium*), AgNPs 8 – common agrimony (*Agrimonia eupatoria*), AgNPs 9 – garden strawberry (*Fragaria ananassa*), AgNPs 10 – purple crownvetch (*Securigera varia*). AgNPs were characterized by absorption spectra (a). The relevant characteristic images of the nanoparticles are shown in the pictures marked with b.

### 3.2 Antioxidant activity of nanoparticles

The antioxidant activity was analyzed by DPPH, ABTS and FRAP methods for AgNPs prepared by green synthesis, and the results were expressed in both DPPH and ABTS methods as percentage of radical scavenging and in FRAP method as percentage of  $\text{Fe}^{3+}$  reduction as well as in all methods as gallic acid equivalent (GAE) in mg/L. Percentage of DPPH and ABTS radical scavenging by AgNPs prepared by green synthesis is shown in Fig. 2A,B and percentage of  $\text{Fe}^{3+}$  reduction measured using FRAP method is shown in Fig. 2C. Results of antioxidant activity of AgNPs determined by DPPH, ABTS and FRAP method and expressed in GAE are shown in Fig. 2D,E,F, respectively.

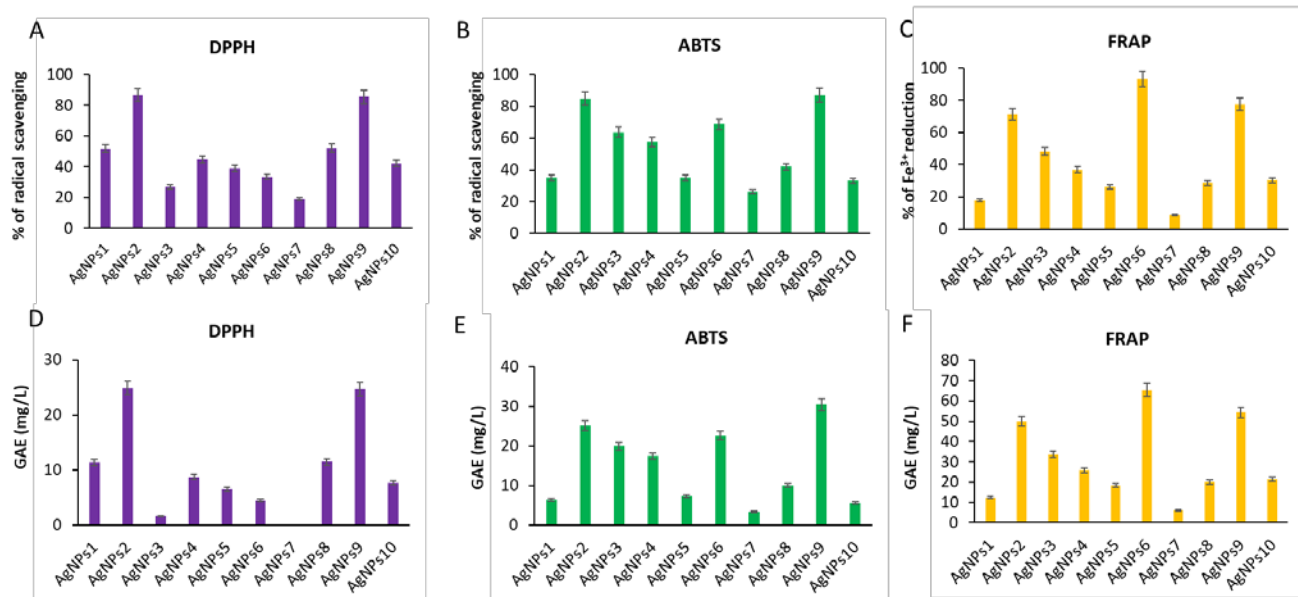

**Fig.2** Antioxidant activity of AgNPs synthesized by green synthesis determined by DPPH method (A, D), ABTS method (B, E) and FRAP method (C,F). AgNPs were prepared using following plant extracts: AgNPs 1 – black tea (*Camelia sinensis*), AgNPs 2 – green tea (*Camelia sinensis*), AgNPs 3 - coffee (*Coffea Arabica*), AgNPs 4 – common thyme (*Thymus vulgaris*), AgNPs 5 – red clover (*Trifolium pratense*), AgNPs 6 – red raspberry (*Rubus idaeus*), AgNPs 7 – absinthe wormwood (*Artemisia absinthium*), AgNPs 8 – common agrimony (*Agrimonia eupatoria*), AgNPs 9 – garden strawberry (*Fragaria ananassa*), AgNPs 10 – purple crownvetch *Securigera varia*.

The highest antioxidant activity was determined in AgNPs 2 (prepared using green tea extract) and in AgNPs 9 (prepared using garden strawberry extract) using DPPH and ABTS methods. Results of antioxidant activity of these samples ranged between 85-87% of radical scavenging and 24-30 GAE (mg/L). When FRAP method was used, the highest antioxidant activity was determined in AgNPs 6 (prepared using red raspberry extract). Result of antioxidant activity of the sample was 93% of radical scavenging and 65 GAE (mg/L).

#### 4. CONCLUSION

Ten different AgNPs were prepared by green synthesis and spectrophotometrically characterized. The spectral maxima ranged between 220-230 nm, 270-290 nm and 470-480 nm. The determination of antioxidant activity using DPPH, ABTS and FRAP methods showed, that the highest antioxidant activity was determined in AgNPs 2 (prepared using green tea extract), AgNPs 9 (prepared using garden strawberry extract), and AgNPs 6 (prepared using red raspberry extract). The antimicrobial and anticancer properties of these AgNPs will be further investigated.

#### ACKNOWLEDGEMENTS

**This work has been funded by the grant IGA GREEN-NANO 316/2018 /FaF and by the grant IGA - ZF/2018 - DP008. CF would like to express his gratitude to RGU for its support.**

#### REFERENCES

- [1] ABOU EL-NOUR, K. M. M., EFTAIHA, A., AL-WARTHAN, A., AMMAR, R. A. A. Synthesis and applications of silver nanoparticles. *Arabian Journal of Chemistry*, 2010, vol. 3, no. 3, pp. 135-140.

- [2] ABDEL-AZIZ, M. S., SHAHEEN, M. S., EL-NEKEETY, A. A., ABDEL-WAHHAB, M. A. Antioxidant and antibacterial activity of silver nanoparticles biosynthesized using *Chenopodium murale* leaf extract. *Journal of Saudi Chemical Society*, 2014, vol. 18, no. 4, pp. 356-363.
- [3] SAXENA, A., TRIPATHI, R. M., SINGH, R. P. Biological synthesis of silver nanoparticles by using onion (*Allium cepa*) extract and their antibacterial activity. *Digest Journal of Nanomaterials and Biostructures*, 2010, vol. 5, no. 2, pp. 427-432.
- [4] MITTAL, A. K., CHISTI, Y., BANERJEE, U. C. Synthesis of metallic nanoparticles using plant extracts. *Biotechnology Advances*, 2013, vol. 31, no. 2, pp. 346-356.
- [5] RAJA, S., RAMESH, V., THIVAHARAN, V. Green biosynthesis of silver nanoparticles using *Calliandra haematocephala* leaf extract, their antibacterial activity and hydrogen peroxide sensing capability. *Arabian Journal of Chemistry*, 2017, vol. 10, no. 2, pp. 253-261.
- [6] GUTTERIDGE, J. M. C. Free-radicals in disease processes - a compilation of cause and consequence. *Free Radical Research Communications*, 1993, vol. 19, no. 3, pp. 141-158.
- [7] HALLIWELL, B., GUTTERIDGE, J. M. C. Role of free radicals and catalytic metal ions in human disease - an overview. *Methods in Enzymology*, 1990, vol. 186, no. pp. 1-85.
- [8] NAZEM, A., MANSOORI, G. A. Nanotechnology solutions for Alzheimer's disease: Advances in research tools, diagnostic methods and therapeutic agents. *Journal of Alzheimers Disease*, 2008, vol. 13, no. 2, pp. 199-223.
- [9] ZHENG, W., WANG, S. Y. Antioxidant activity and phenolic compounds in selected herbs. *Journal of Agricultural and Food Chemistry*, 2001, vol. 49, no. 11, pp. 5165-5170.